

AD735687



COPY NO. 49

TECHNICAL REPORT 4261

APPLICATION OF SUPERPOSITION TECHNIQUES  
TO  
THERMAL DEGRADATION OF EPOXIDE RESINS

H. T. LEE  
ELISE MCABEE  
DAVID W. LEVI

DECEMBER 1971

APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED.

PICATINNY ARSENAL  
DOVER, NEW JERSEY

Reproduced by  
NATIONAL TECHNICAL  
INFORMATION SERVICE  
Springfield, Va. 22151

DDC  
RECEIVED  
JAN 25 1972  
C 39

The findings in this report are not to be construed as an official Department of the Army position.

#### DISPOSITION

Destroy this report when no longer needed. Do not return it to the originator.

ACCESSION NO.	
CPSTI	WHITE SECTION <input checked="" type="checkbox"/>
DOC	DIFF SECTION <input type="checkbox"/>
CHANGED	<input type="checkbox"/>
JUSTIFICATION	
BY	
DISTRIBUTION/AVAILABILITY CODES	
REST.	AVAIL. AND BY SPECIAL
A	

UNCLASSIFIED

Security Classification

## DOCUMENT CONTRL DATA - R &amp; D

(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

1. ORIGINATING ACTIVITY (Corporate author)		2a. REPORT SECURITY CLASSIFICATION	
Picatinny Arsenal, Dover, N. J. 07801		UNCLASSIFIED	
		2b. GROUP	
3. REPORT TITLE			
APPLICATION OF SUPERPOSITION TECHNIQUES TO THERMAL DEGRADATION OF EPOXIDE RESINS			
4. DESCRIPTIVE NOTES (Type of report and inclusive dates)			
5. AUTHOR(S) (First name, middle initial, last name)			
H. T. Lee Elise McAbee David W. Levi			
6. REPORT DATE		7a. TOTAL NO. OF PAGES	7b. NO. OF REFS
DECEMBER 1971		41	9
8a. CONTRACT OR GRANT NO.		8b. ORIGINATOR'S REPORT NUMBER(S)	
b. PROJECT NO. DA 1T062105A32907		Technical Report 4261	
c. AMCMS Code 502E.11.29507		9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
d.			
10. DISTRIBUTION STATEMENT			
Approved for public release; distribution unlimited.			
11. SUPPLEMENTARY NOTES		12. SPONSORING MILITARY ACTIVITY	
13. ABSTRACT			
<p>Time-temperature superposition was successfully applied to thermogravimetric (TGA) data for the thermal degradation of a number of cured epoxide resins. For several epoxides and for two curing agents, the same values of <math>\log a_D</math> were applicable. This suggests that the same chemical processes were occurring in all cases, at least up to conversions of about 50%. Since <math>\log a_D</math> was linear with temperature, it also was possible to superpose W versus <math>\log T</math> plots at various rates of heating. Once more, the same shift factors (<math>\log K</math>) could be applied to all the epoxides studied.</p>			

DD FORM 1473

REPLACES DD FORM 1473, 1 JAN 66, WHICH IS OBSOLETE FOR ARMY USE.

UNCLASSIFIED

Security Classification

UNCLASSIFIED

Security Classification

4. KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
Epoxides Superposition Thermal degradation Thermogravimetric analysis Shift factor Master curve						

UNCLASSIFIED

Security Classification

Technical Report 4261

APPLICATION OF SUPERPOSITION TECHNIQUES TO THERMAL  
DEGRADATION OF EPOXIDE RESINS

by

H. T. Lee  
Elise McAbee  
David W. Levi

December 1971

Approved for public release; distribution unlimited

AMCMS Code 502E.11.29507  
DA Project No. 1T062105A32907

Materials Engineering Division  
Feltman Research Laboratory  
Picatinny Arsenal  
Dover, N.J.

The citation in this report of the trade names of commercially available products does not constitute official indorsement or approval of the use of such products.

## TABLE OF CONTENTS

	Page No.
Object	1
Abstract	1
Introduction	2
Results and Discussion	2
Conclusion	5
References	5
Distribution List	31
Tables	
1 List of epoxides studied	6
Figures	
1 Weight loss of DER 332 as a function of time	7
2 Master curve of weight loss versus reduced time for DER 332. Constructed from Fig 1 using the log $a_D$ terms on the graph	8
3 Weight loss of Epon 820 as a function of time	9
4 Master curve of weight loss versus reduced time for Epon 820. Constructed from Fig 3 using the log $a_D$ terms on the graph	10
5 Weight loss of Heptyl as a function of time	11
6 Master curve of weight loss versus reduced time for Heptyl. Constructed from Fig 5 using the log $a_D$ terms on the graph	12

7	Weight loss of Undecyl as a function of time	13
8	Master curve of weight loss versus reduced time for Undecyl. Constructed from Fig 7 using the $\log a_D$ terms on the graph	14
9	Weight loss of Pentadecyl as a function of time	15
10	Master curve of weight loss versus reduced time for Pentadecyl. Constructed from Fig 9 using the $\log a_D$ terms on the graph	16
11	Weight loss of halogenated 6F as a function of time	17
12	Master curve of weight loss versus reduced time for halogenated 6F. Constructed from Fig 11 using the $\log a_D$ terms on the graph	18
13	Weight loss of Undecyl (HMDA cured) as a function of time	19
14	Master curve of weight loss versus reduced time for HMDA cured Undecyl. Constructed from Fig 13 using the $\log a_D$ terms on the graph	20
15	Arrhenius plot of shift factors for determination of activation energy	21
16	Shift factors versus temperature for the cured epoxide resins	22
17	Shift factor versus rate of heating	23
18	Master curve of weight loss versus temperature for DER 332	24
19	Master curve of weight loss versus temperature for Epon 820	25
20	Master curve of weight loss versus temperature for Heptyl	26



21	Master curve of weight loss versus temperature for Undecyl	27
22	Master curve of weight loss versus temperature for Pentadecyl	28
23	Master curve of weight loss versus temperature for halogenated 6F	29
24	Master curve of weight loss versus temperature for HMDA cured Undecyl	30

## OBJECT

The object of this study was to apply temperature-time superposition to thermogravimetric (TGA) data involving the thermal degradation of epoxide resins.

## ABSTRACT

Time-temperature superposition was successfully applied to thermogravimetric (TGA) data for the thermal degradation of a number of cured epoxide resins. For several epoxides and for two curing agents, the same values of  $\log a_D$  were applicable. This suggests that the same chemical processes were occurring in all cases, at least up to conversions of about 50%. Since  $\log a_D$  was linear with temperature, it also was possible to superpose  $W$  versus  $\log T$  plots at various rates of heating. Once more, the same shift factors ( $\log K$ ) could be applied to all the epoxides studied.

## INTRODUCTION

A widely used method of studying the thermal degradation of polymers involves measuring the volatiles given off by recording weight loss as a function of time and temperature. At least in certain cases, it should be possible to apply superposition methods in the treatment of such thermogravimetric analysis (TGA) data (Ref 1, 2). This report describes such an application to TGA results obtained in these laboratories for a number of epoxide polymers.

## RESULTS AND DISCUSSION

A temperature-time superposition method should be valid for any rate process where the temperature influences only the rate constant  $k$ . Even where the effect of temperature is more complicated, it usually is to be expected that the major temperature dependence is through the rate constant (Ref 1, 2).

If  $k_0$  is the rate constant at the reference temperature and  $k$  the rate constant at any other temperature, then  $\log (k/k_0) = \log a_D$  is the amount by which the data must be shifted along the log to axis. The rate constant is conventionally written

$$k = Ae^{-\Delta H/RT} \quad (1)$$

Then the ratio of rate constants for temperatures  $T$  and  $T_0$  is

$$\log (k/k_0) = \log a_D = -\frac{\Delta H}{2.303R} \left( \frac{1}{T} - \frac{1}{T_0} \right) \quad (2)$$

where  $\Delta H$  is the activation energy and  $R$  is the gas constant.

Thermogravimetric data for several epoxide polymers have been obtained in these laboratories over the past few years (Refs 3 through 7). These data were used to test the validity of applying the superposition method to TGA curves.

The epoxides studied and the abbreviations that will be used in this report for them are shown in Table 1 (Ref 5). Each epoxide was cured with m-phenylenediamine (MPD) as described in the earlier reports (Ref 3, 4). In one case, the undecyl was cured with hexamethylenediamine (HMDA) (Ref 3).

The primary thermograms (Ref 3, 4) had been obtained as weight loss versus temperature traces at several rates of heating. Such curves, due to the usual nonlinear temperature dependence of the shift factor (Ref 8), would not be expected to be superposable by horizontal shifts along the temperature axis. However, since traces for several rates of heating were available (Ref 3, 4), it was possible to plot weight loss versus log time from the information in the primary curves. Such plots are shown for DER 332 in Figure 1. These weight loss curves were shifted to the 400° C curve along the log time axis to give the curve shown in Figure 2. The shift distances along the log time scale are denoted  $\log a_D$  (Ref 1). Figure 2 does indicate that a time-temperature superposition applies to this type of data. Figures 3 through 12 show the corresponding plots for the other MPD cured epoxides listed in Table 1. Figures 13 and 14 give the results for the undecyl epoxide cured with HMDA.

It is noteworthy that the same shift factors ( $a_D$ ) could be used in constructing master curves, despite the structural differences in the epoxides. This was also true in the one case where the curing agent was changed; and it would seem to indicate that the degradation was following the same course in each case, the primary process not depending on structural changes that were introduced into this series of polymers. In earlier work (Ref 3, 5), it was found that activation energy values for the degradation of MPD cured epoxides were essentially constant within the experimental error. This also indicated that chemical processes occurring in the degradation were the same for all the polymers. It is known that degradation of cured epoxide resins during early stages primarily involves destruction of the aromatic ether moieties (Ref 5, 9). The thermograms used in the present work are reliable up to around 50% degradation (Ref 3). Above this degree of conversion, deposition of material on the balance weighing system made the results somewhat suspect. So it would appear that the data obtained probably mainly reflects changes in the ether moiety. It is believed that such changes will be little affected by steric factors arising from side-chain effects (Ref 3, 5).

The same conclusions appear to hold for the single HMDA cured sample. As indicated above, the same  $a_D$  values that were used for the MPD cured samples could also be applied to this material. Lee, Reich, and Levi (Ref 3) found that in this case the activation energy for degradation appeared to some 15% lower than that for MPD cured epoxides. On the basis of the limited data at their disposal, however, they could not be certain whether this was a real effect or only experimental error. Our results here tend to support the latter view.

A plot of  $\log a_D$  versus  $1/T$  according to Equation (2) is shown in Figure 15. An activation energy of 15 kcal/mole was found from the Arrhenius plots for all of the cured epoxides studied. This constancy is to be expected if the same degradation processes are operating in all cases over the conversion range investigated.

Most kinetic parameters evaluated from TGA data based on the reaction rate equations were weight dependent. The prime parameters in these equations were concentrations expressed in terms of weight changes. The implication of weight dependency possibly would affect the values of the evaluated kinetic parameters. This probably would account for the differences between the values for the activation energy obtained in the present study and those from earlier work.

Figure 16 shows the temperature dependence of  $\log a_D$ . The fact that  $\log a_D$  is linear with temperature suggests that superposition might be applicable to  $W$  versus  $\log T$  plots at various rates of heating (Ref 8). Visual inspection of such plots also indicated that they were nearly parallel.

Shift factors, designated in this case, as  $K$  for superposing the weight loss-log temperature plots were determined by inspection for each of the epoxides. Upon plotting the average  $\log K$  values against rate of heating (RH), the curve shown in Figure 17 then were used in constructing the master curves shown in Figures 18 through 24. It appears that the superposition procedure is applicable to these curves and that the same  $\log K$  values can be applied to all of them. This demonstrates once more that the same chemical processes seem to be occurring in the thermal degradation of all the epoxide resins studied.

## CONCLUSION


Time-temperature superposition can be applied to thermogravimetric data for cured epoxide resins.

## REFERENCES


1. J. C. Halpin, AFML-TR-67-423, June 1969
2. S. W. Tsai, Mechanics of Composite Materials, Proc. 5th Symposium on Naval Structural Mechanics, Edited by F. W. Wendt, H. Liebowitz and N. Perrone, Pergamon, 1970
3. H. T. Lee, L. Reich, and D. W. Levi, Picatinny Arsenal Technical Report 3197, December 1964
4. H. T. Lee, L. Reich, and D. W. Levi, Picatinny Arsenal Technical Report 3194, May 1965
5. D. W. Levi, L. Reich, and H. T. Lee, Polymer Eng. and Sci. 5 (3), 135 (1965)
6. H. T. Lee, Picatinny Arsenal Technical Report 3624 February 1968
7. H. T. Lee and D. W. Levi, J. Appl. Polymer Sci. 13, 1703 (1969)
8. J. D. Ferry, Viscoelastic Properties of Polymers, John Wiley and Sons, Inc., N.Y., 1970, pp 343-344
9. L. H. Lee, Am. Chem. Soc., Div. Polymer Chem., Polymer Preprints 5, No. 2, 453 (1964)

TABLE 1

List of epoxides studied

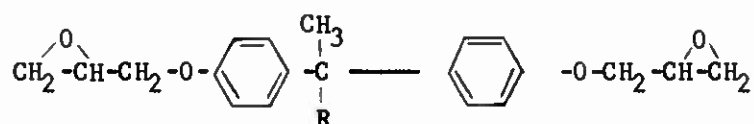

<u>R</u>	<u>Abbreviation</u>
-CH <sub>3</sub>	Epon 820
-CH <sub>3</sub>	DER 332
-(CH <sub>2</sub> ) <sub>6</sub> CH <sub>3</sub>	Heptyl
-(CH <sub>2</sub> ) <sub>10</sub> CH <sub>3</sub>	Undecyl
-(CH <sub>2</sub> ) <sub>14</sub> CH <sub>3</sub>	Pentadecyl



Halogenated 6F

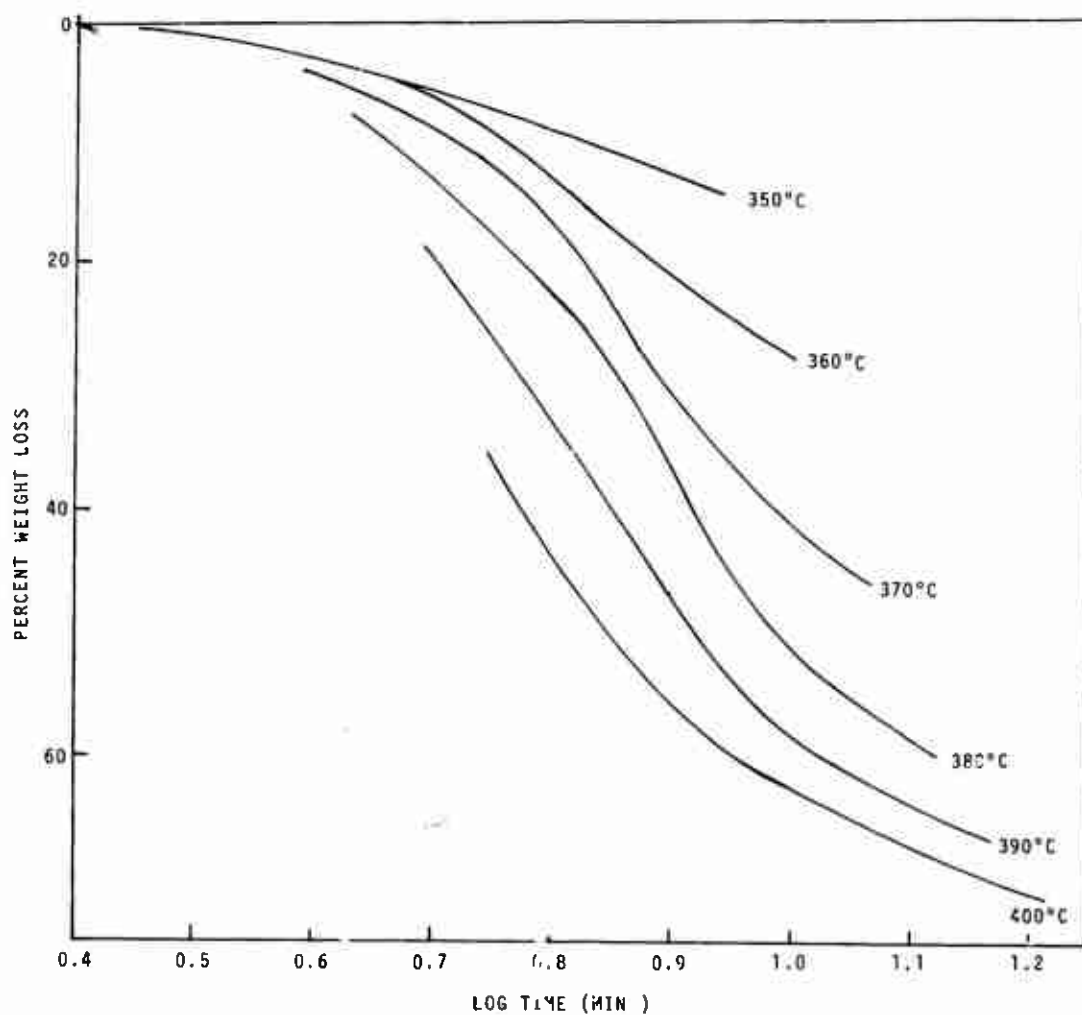


Fig 1 Weight loss of DER 332 as a function of time



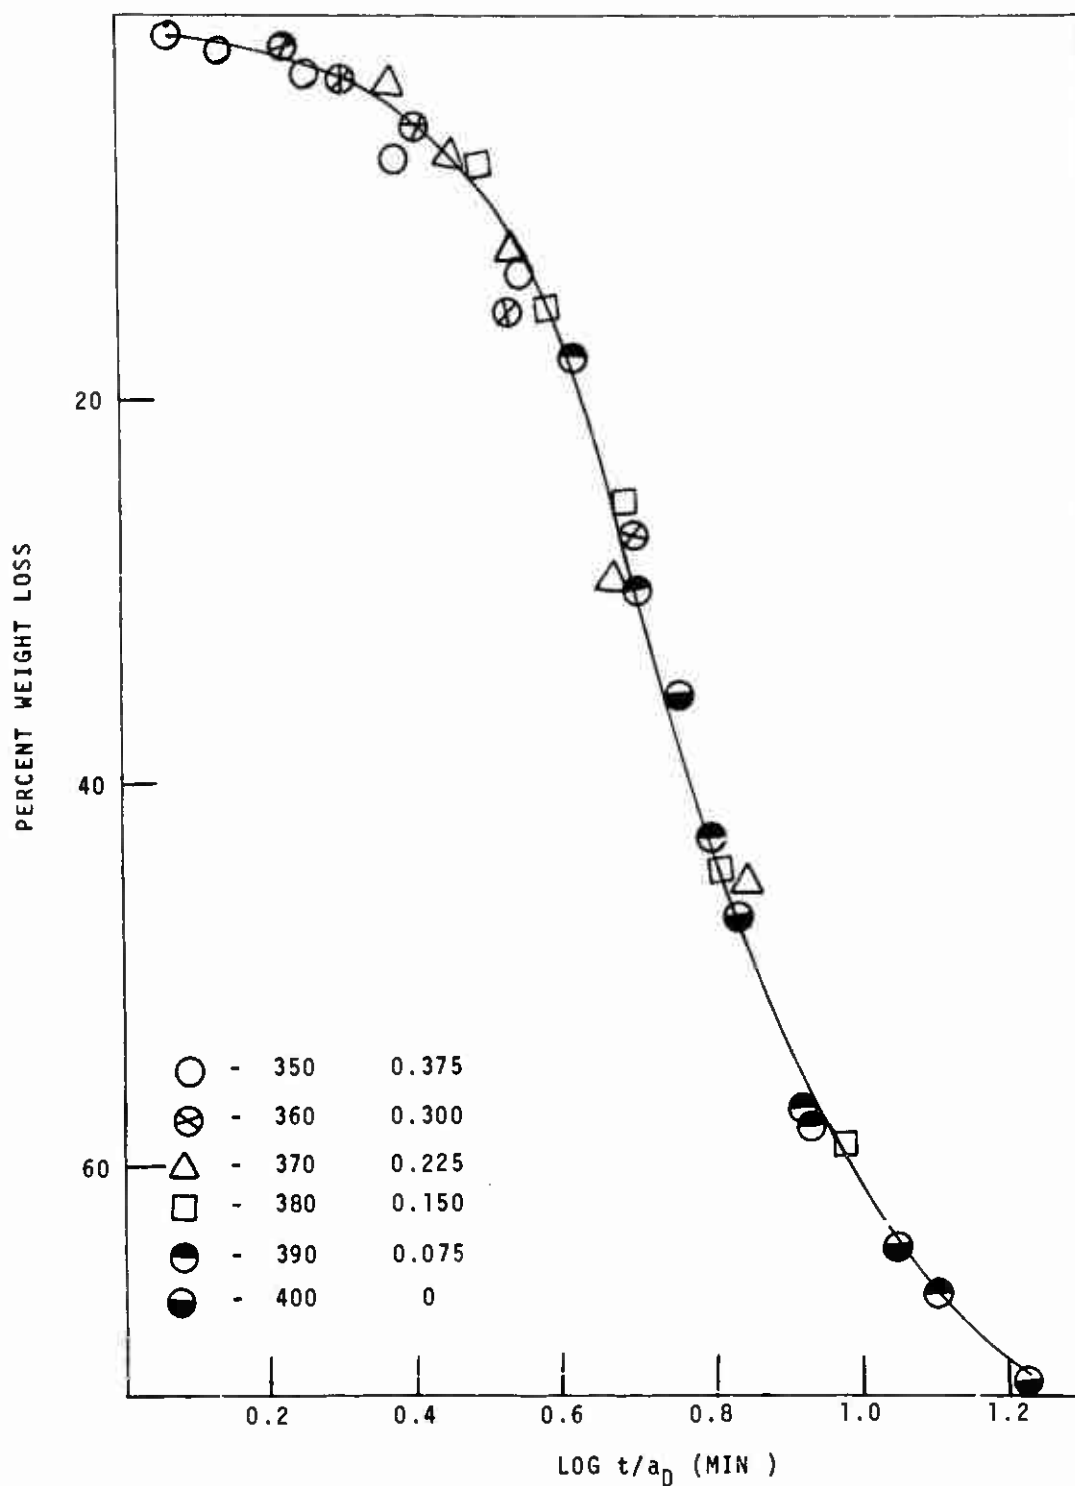


Fig 2 Master curve of weight loss versus reduced time for DER 332. Constructed from Fig 1 using the  $\log a_D$  terms on the graph

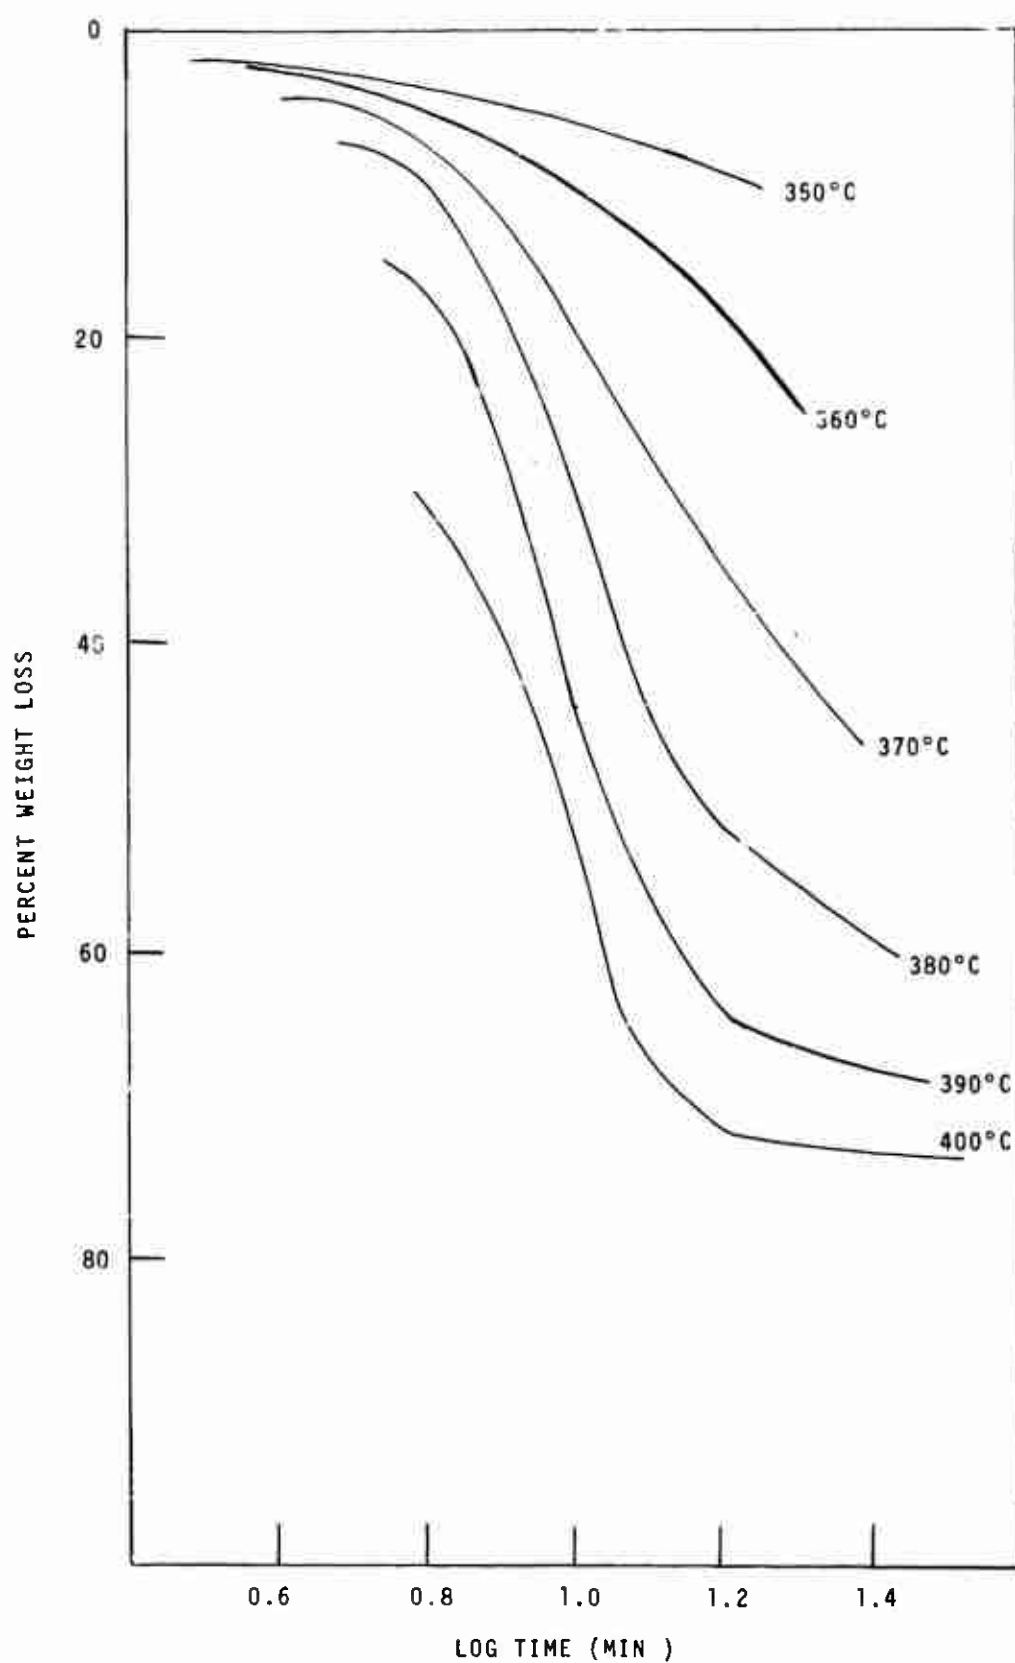


Fig 3 Weight loss of Epon 820 as a function of time

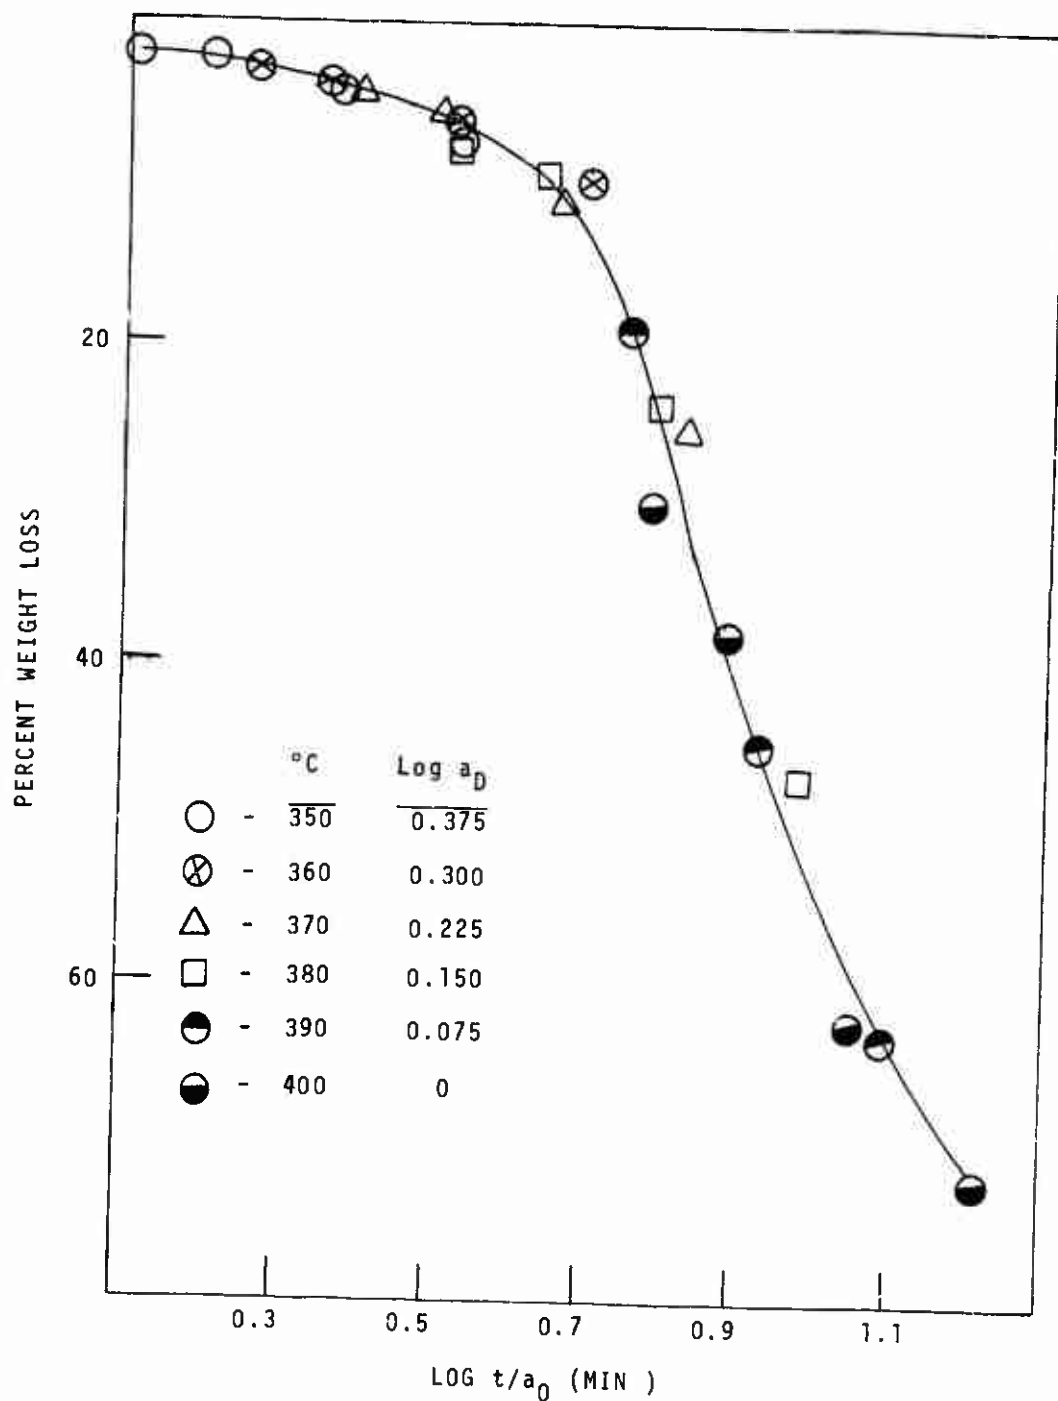


Fig 4 Master curve of weight loss versus reduced time for Epon 820. Constructed from Fig 3 using the  $\log a_D$  terms on the graph

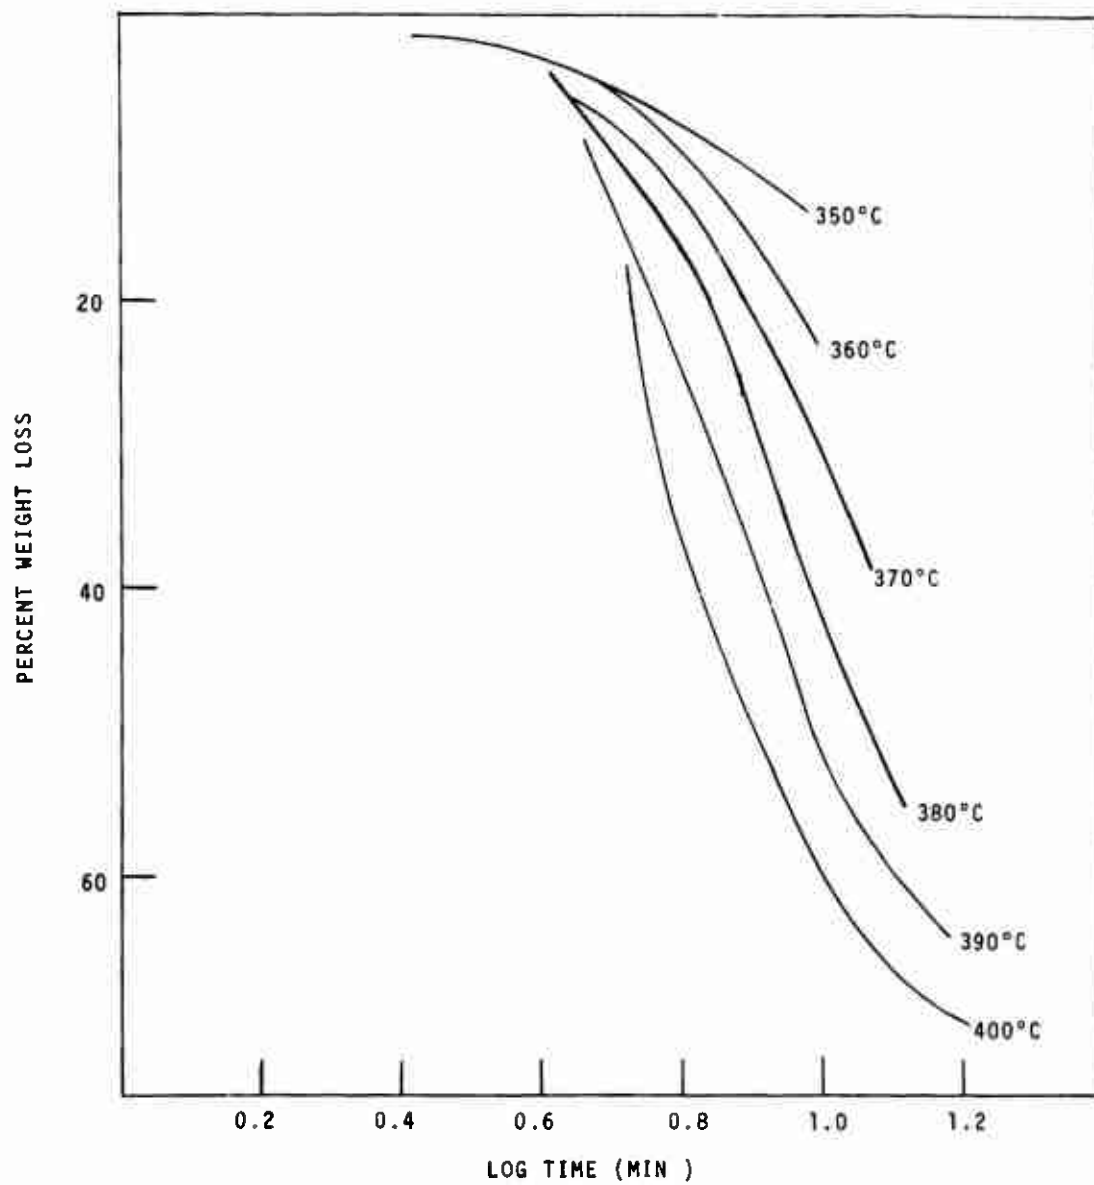


Fig 5 Weight loss of Heptyl as a function of time

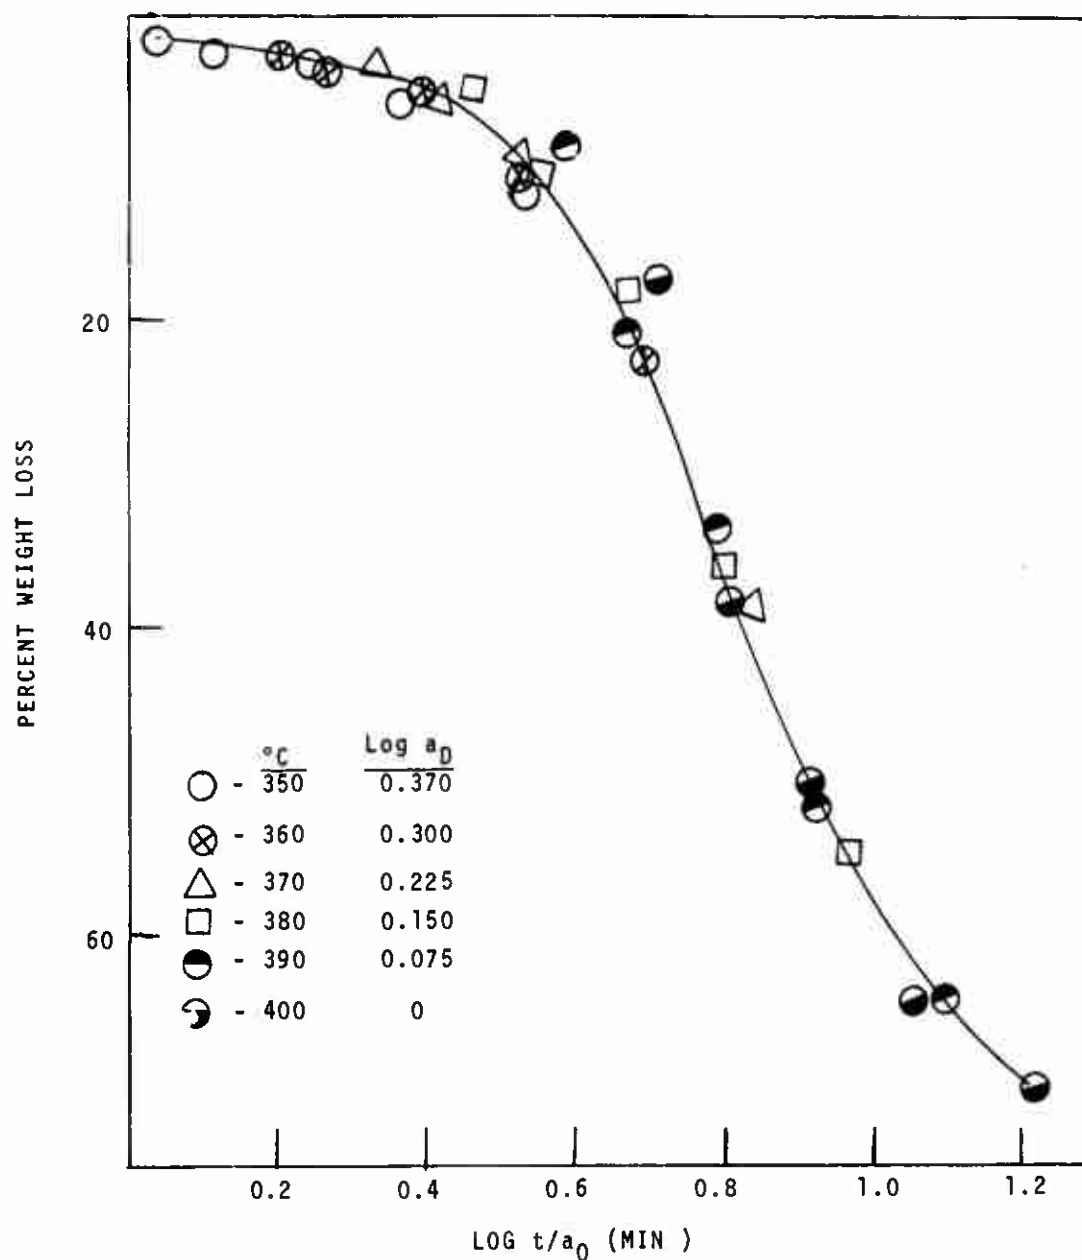


Fig 6 Master curve of weight loss versus reduced time for Heptyl.  
Constructed from Fig 5 using the  $\log a_D$  terms on the graph

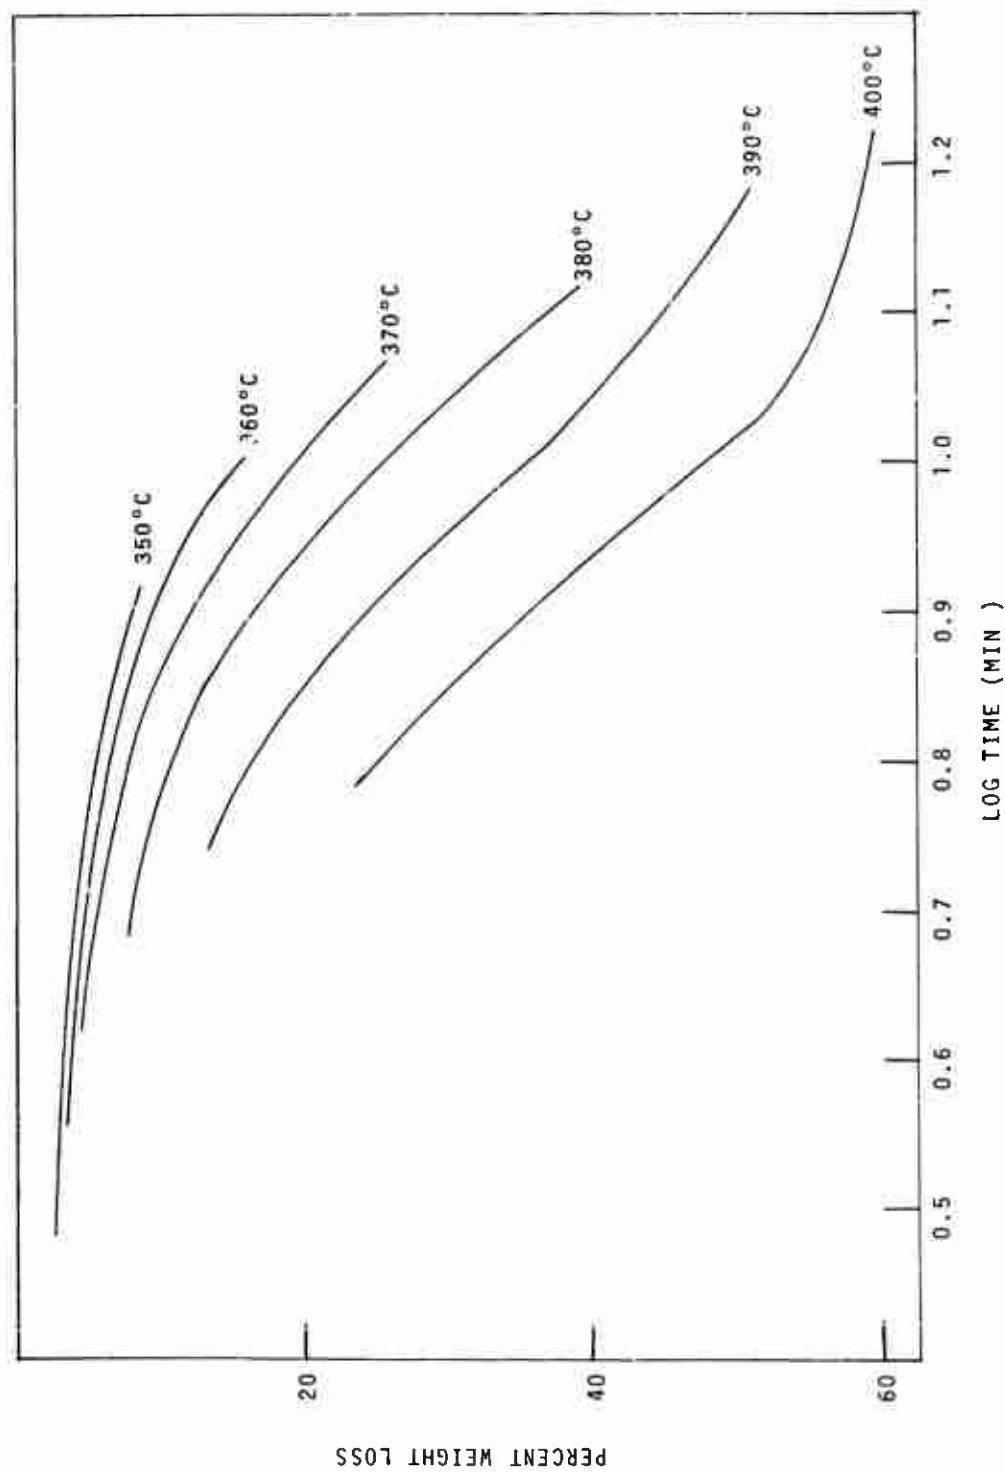


Fig 7 Weight loss of Undecyl as a function of time

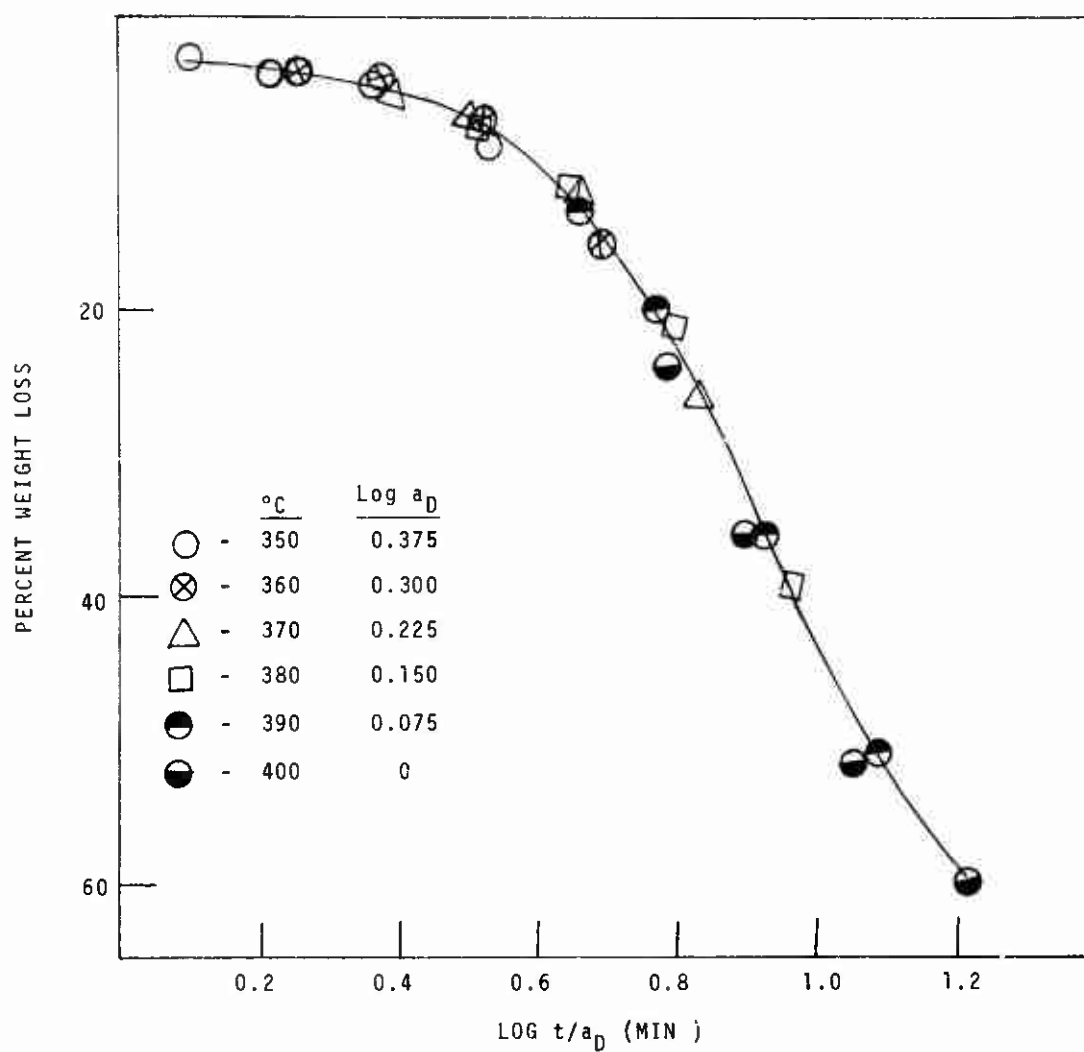


FIG. 8 Master curve of weight loss versus reduced time for Undecyl.  
Constructed from Fig. 7 using the  $\log a_D$  terms on the graph

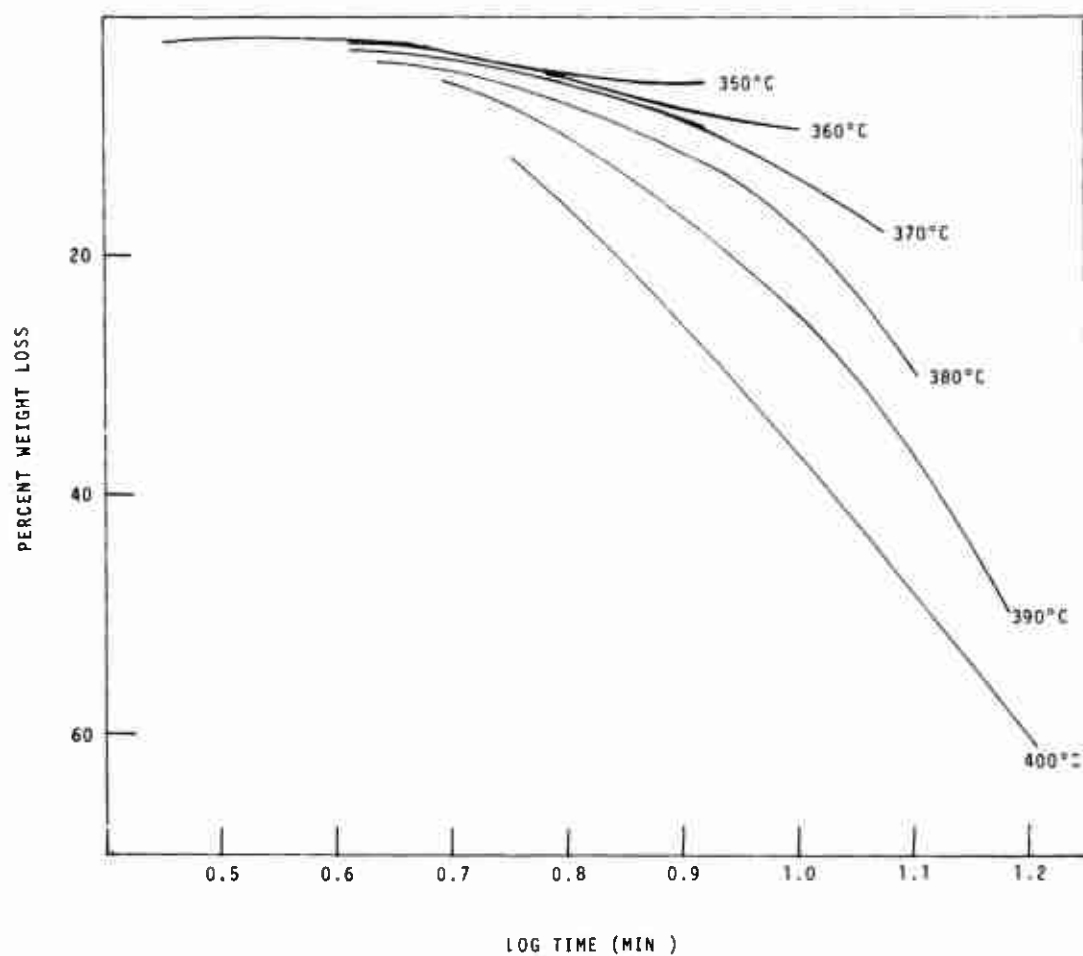


Fig 9 Weight loss of Pentadecyl as a function of time



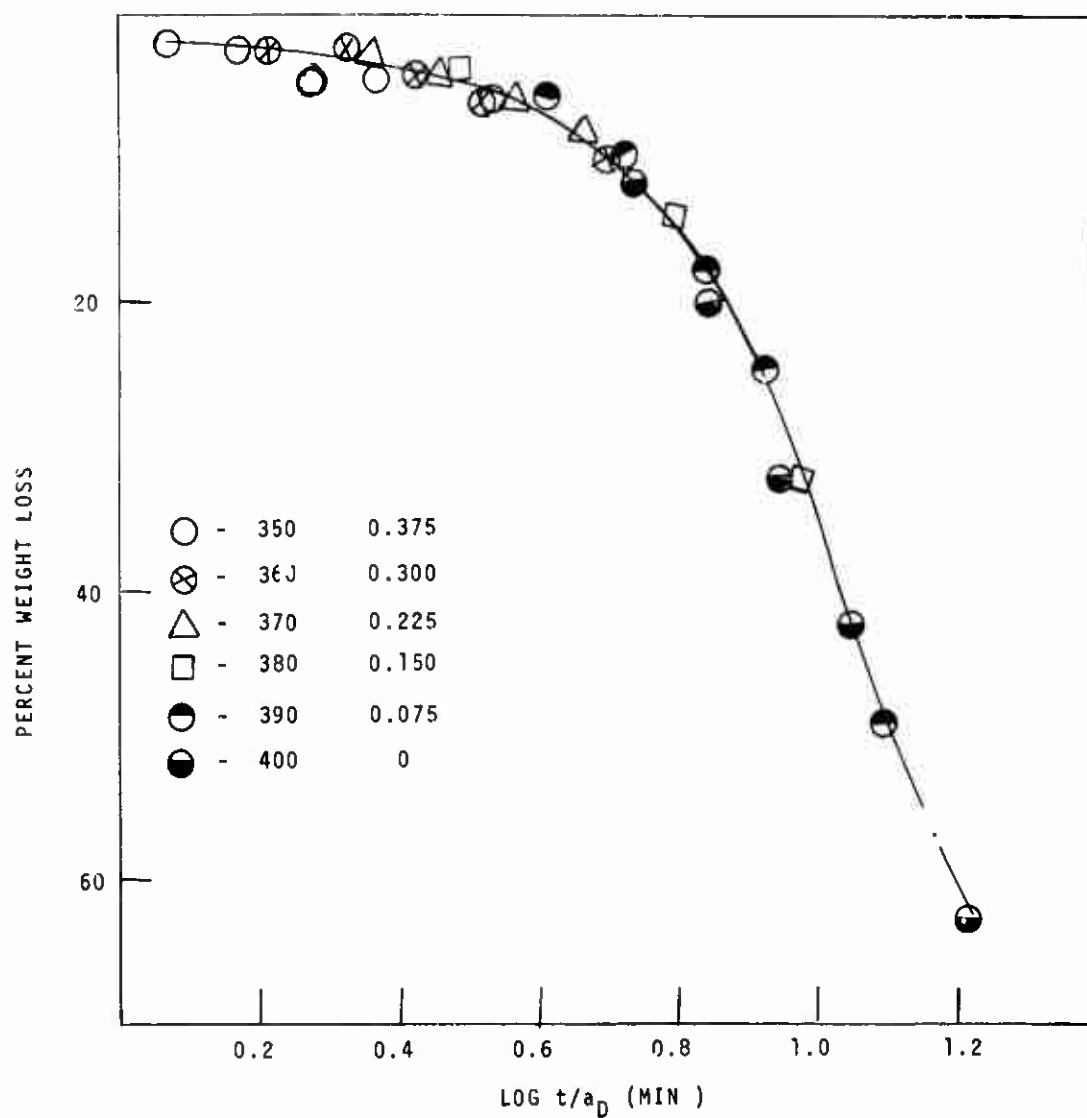


Fig 10 Master curve of weight loss versus reduced time for Pentadecyl. Constructed from Fig 9 using the  $\log a_D$  terms on the graph

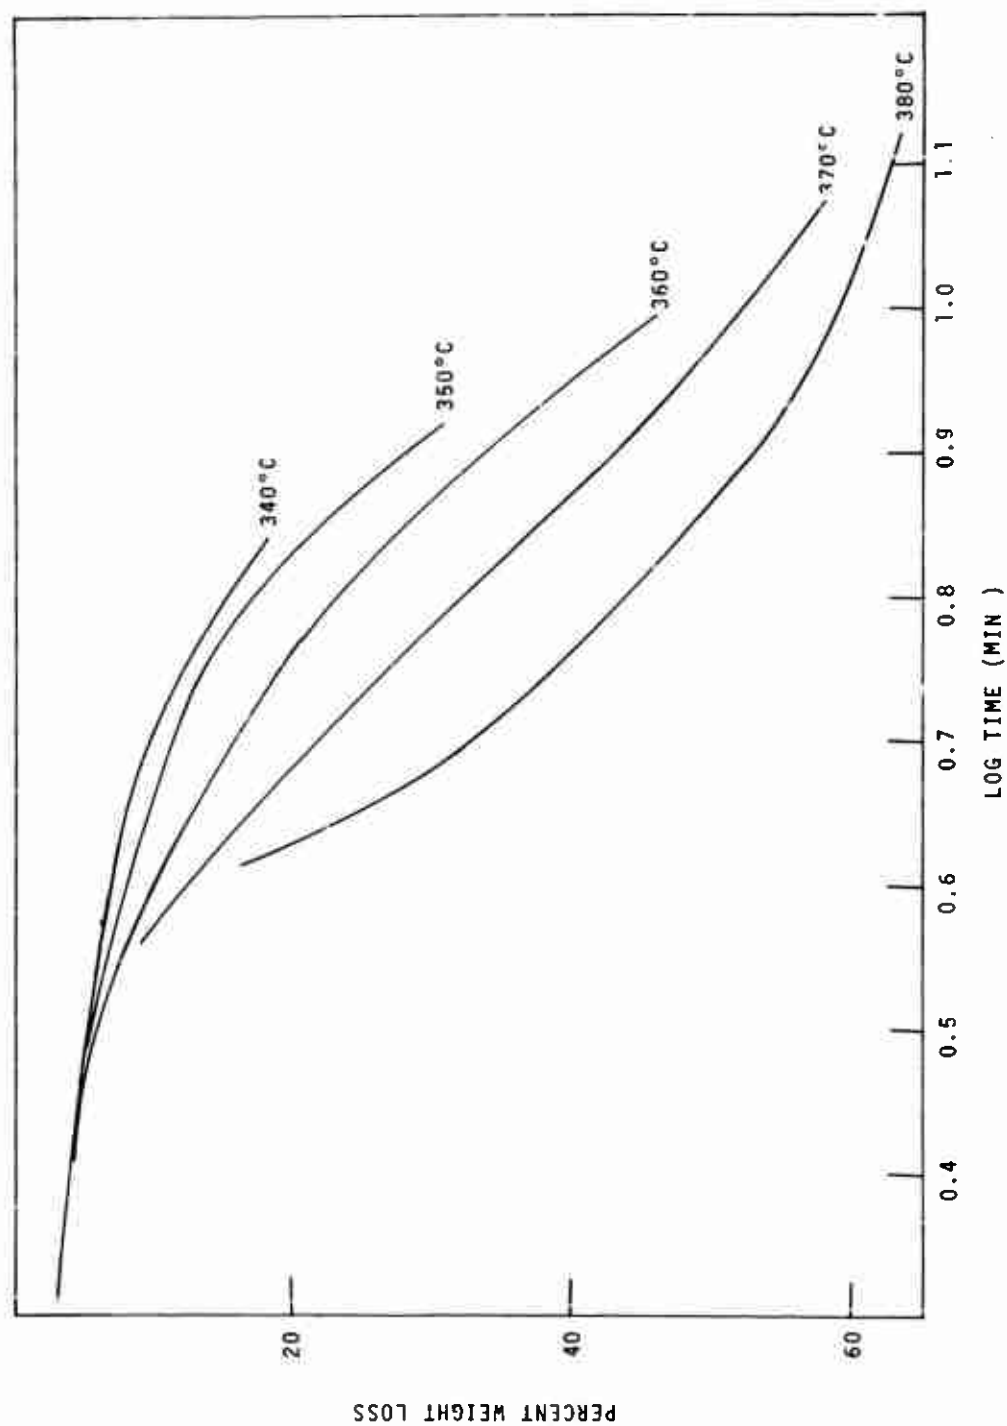


Fig 11 Weight loss of halogenated 6F as a function of time

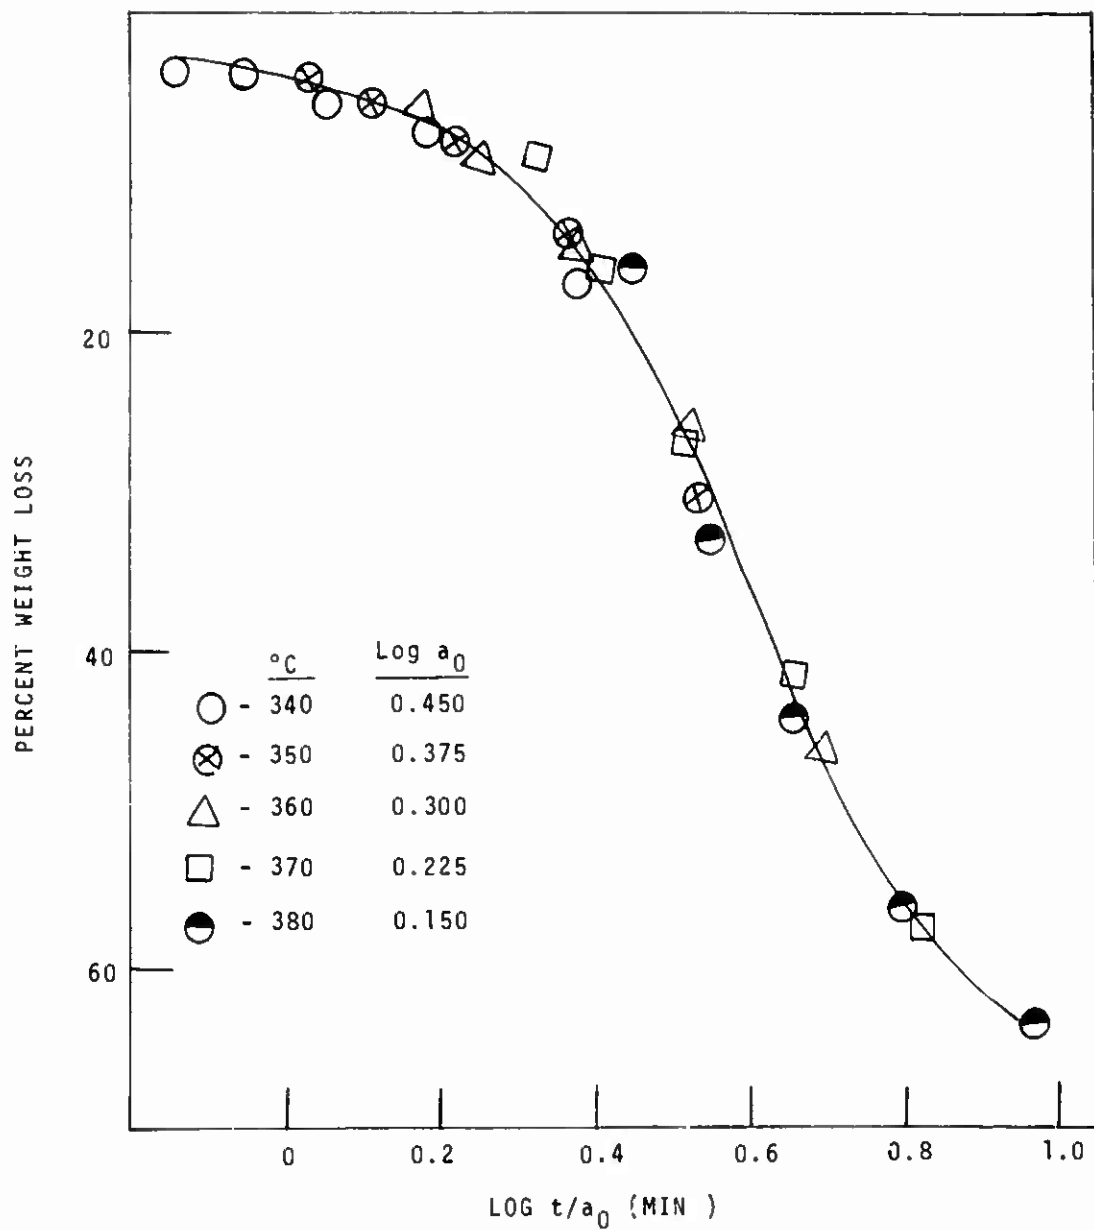


Fig 12 Master curve of weight loss versus reduced time for halogenated 6F. Constructed from Fig 11 using the  $\log a_0$  Terms on the graph

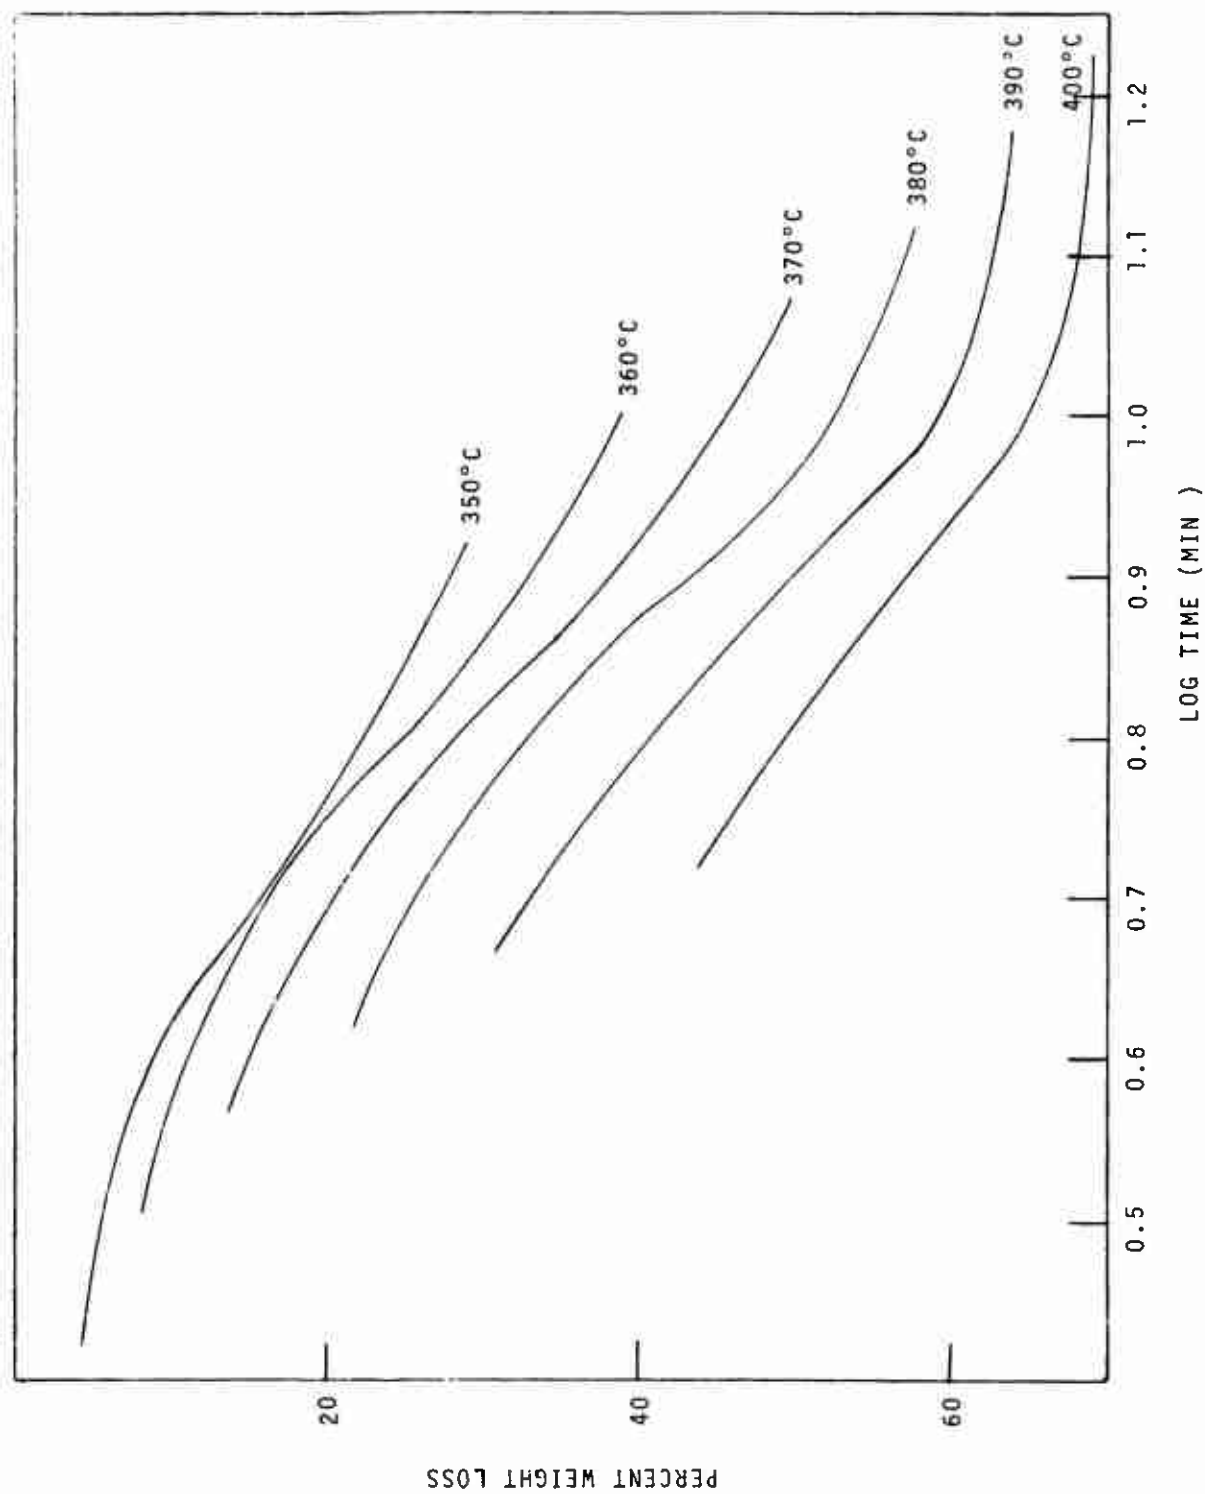


Fig 13 Weight loss of Undecyl (HMDA cured) as a function of time

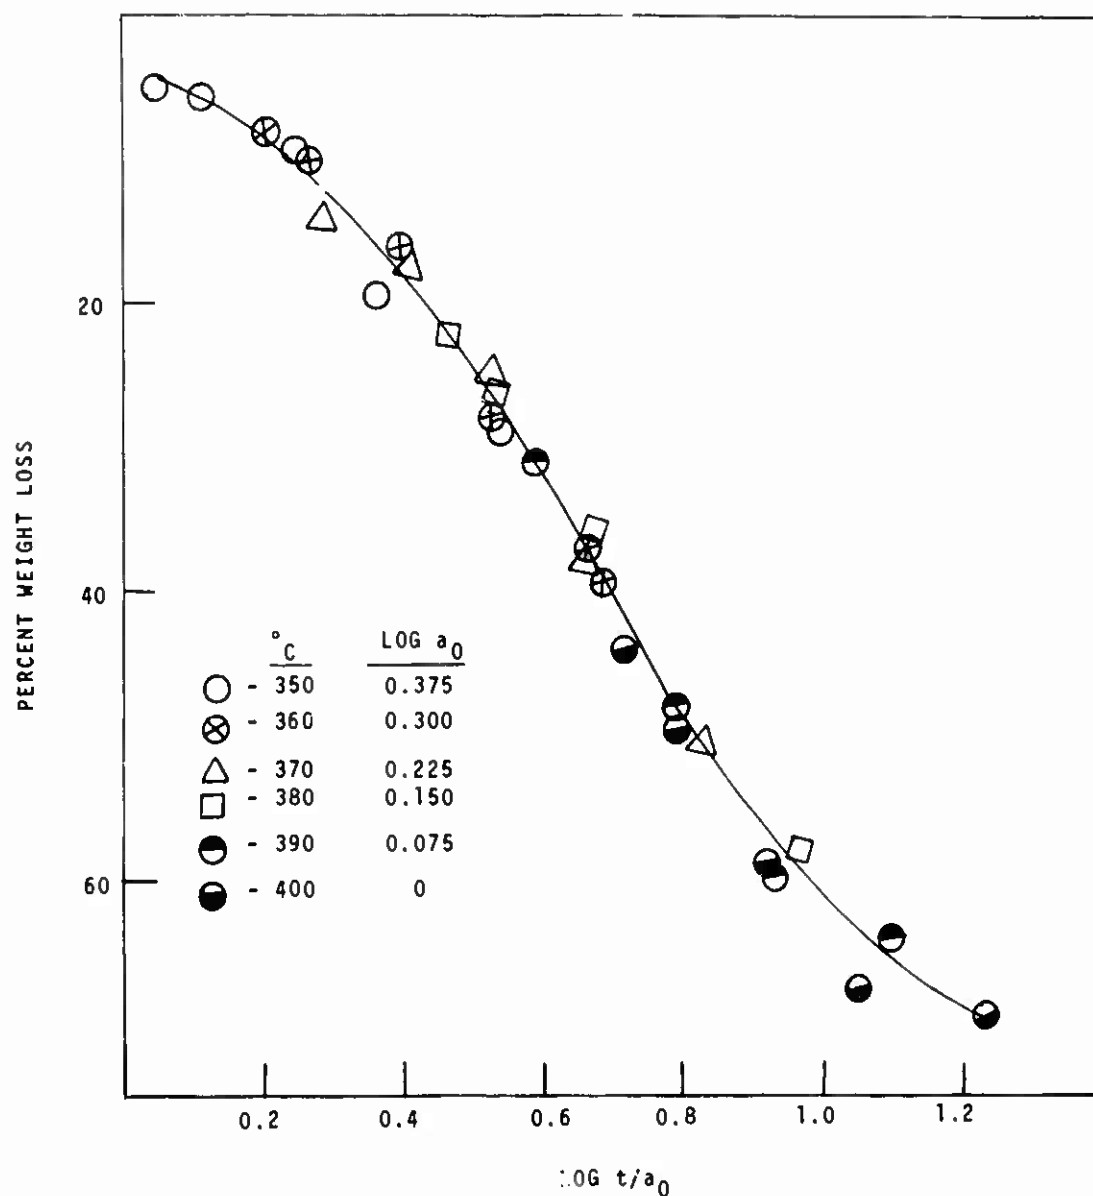


Fig 14 Master curve of weight loss versus reduced time for HMDA cured Undecyl. Constructed from Fig 13 using the  $\log a_0$  terms on the graph

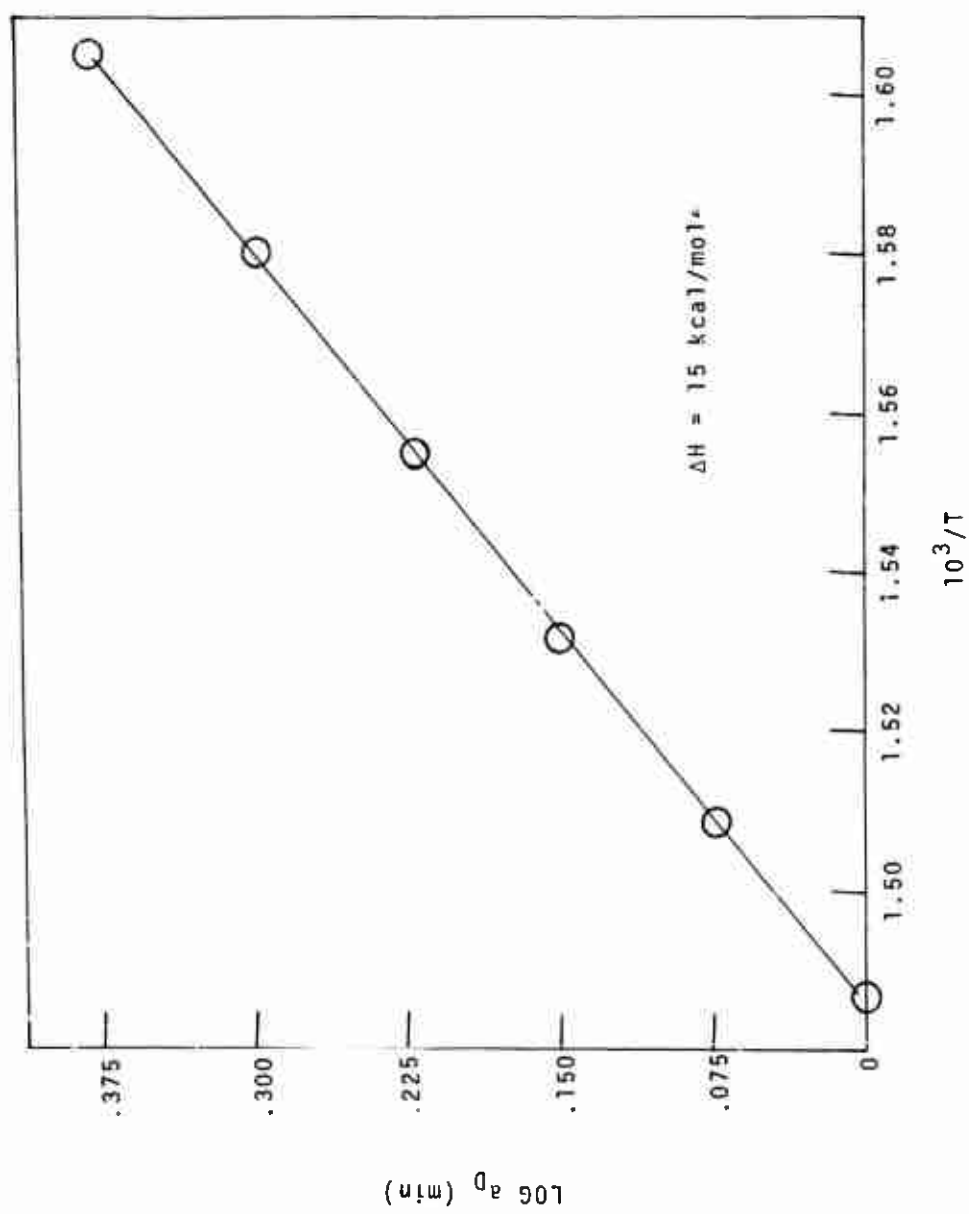


Fig 15 Arrhenius plot of shift factors for determination of activation energy

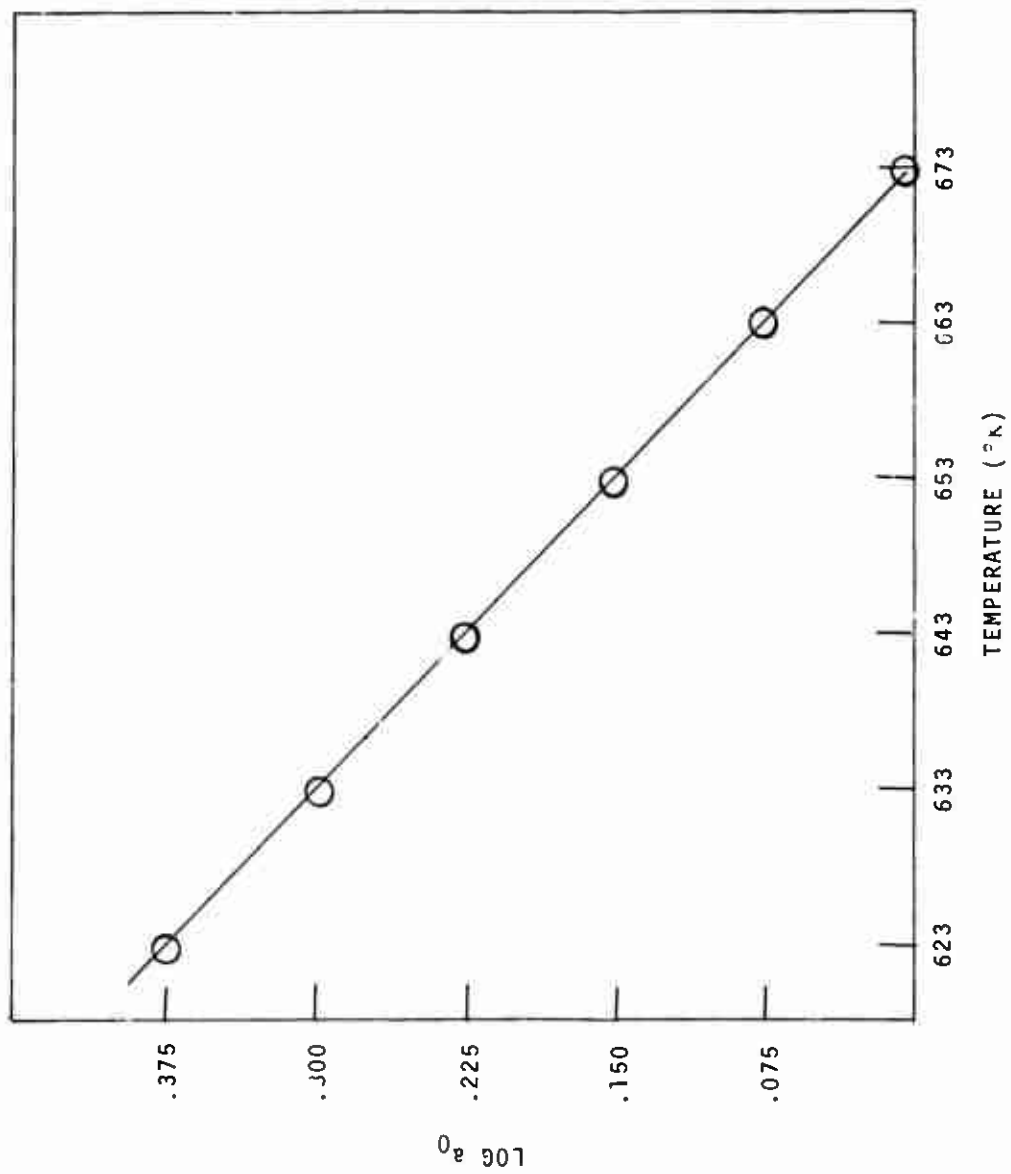


Fig 16 Shift factors versus temperature for the cured epoxide resins

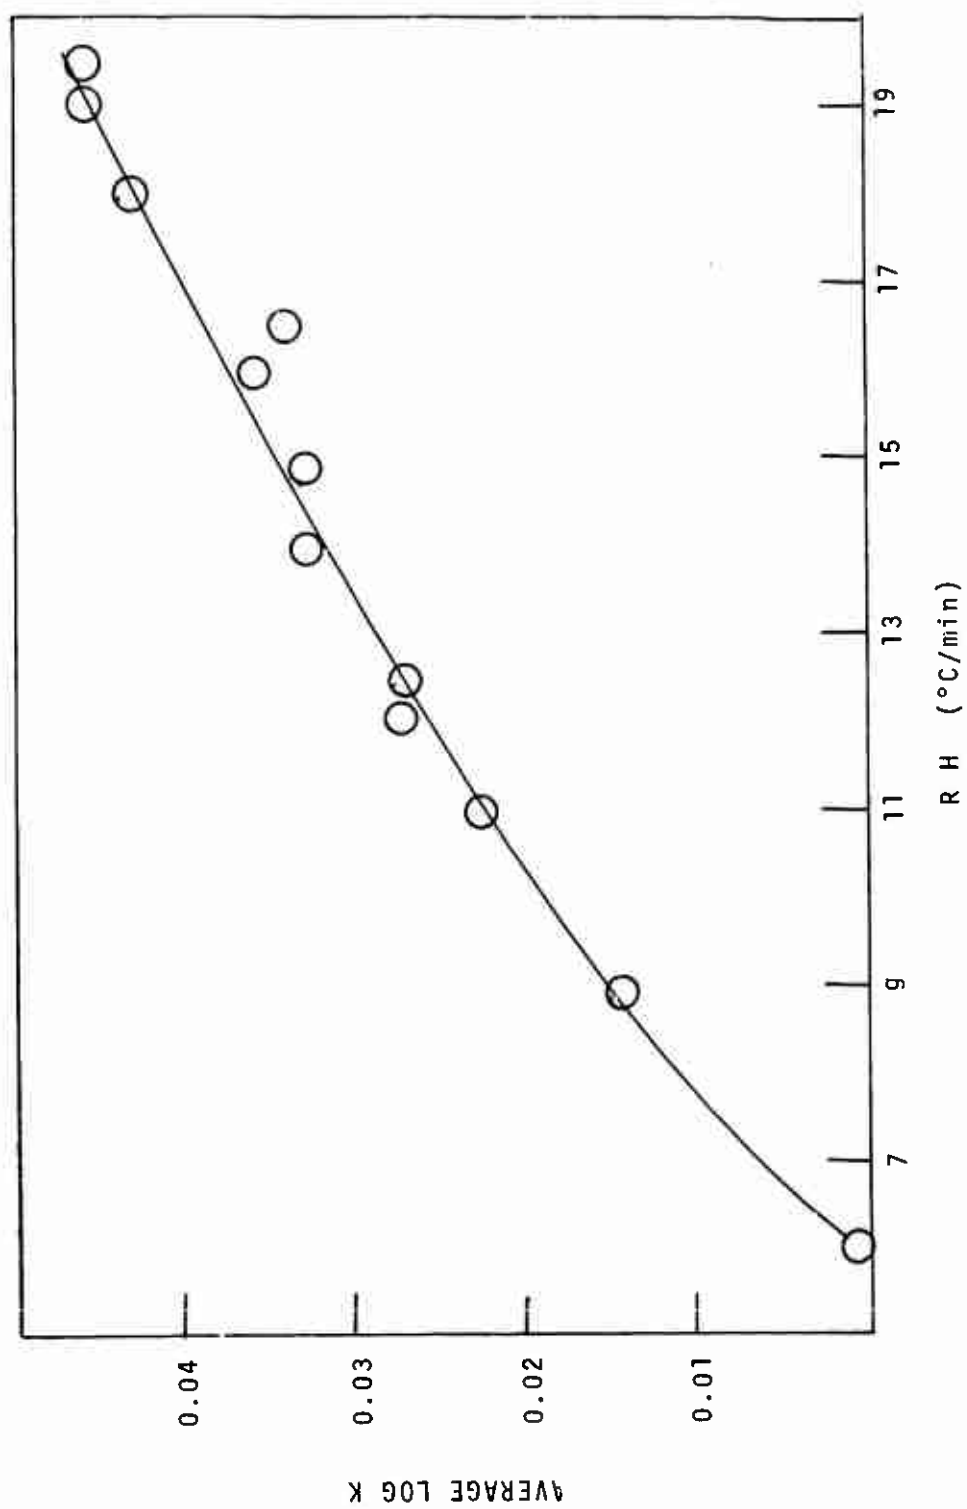


Fig 17 Shift factor versus rate of heating



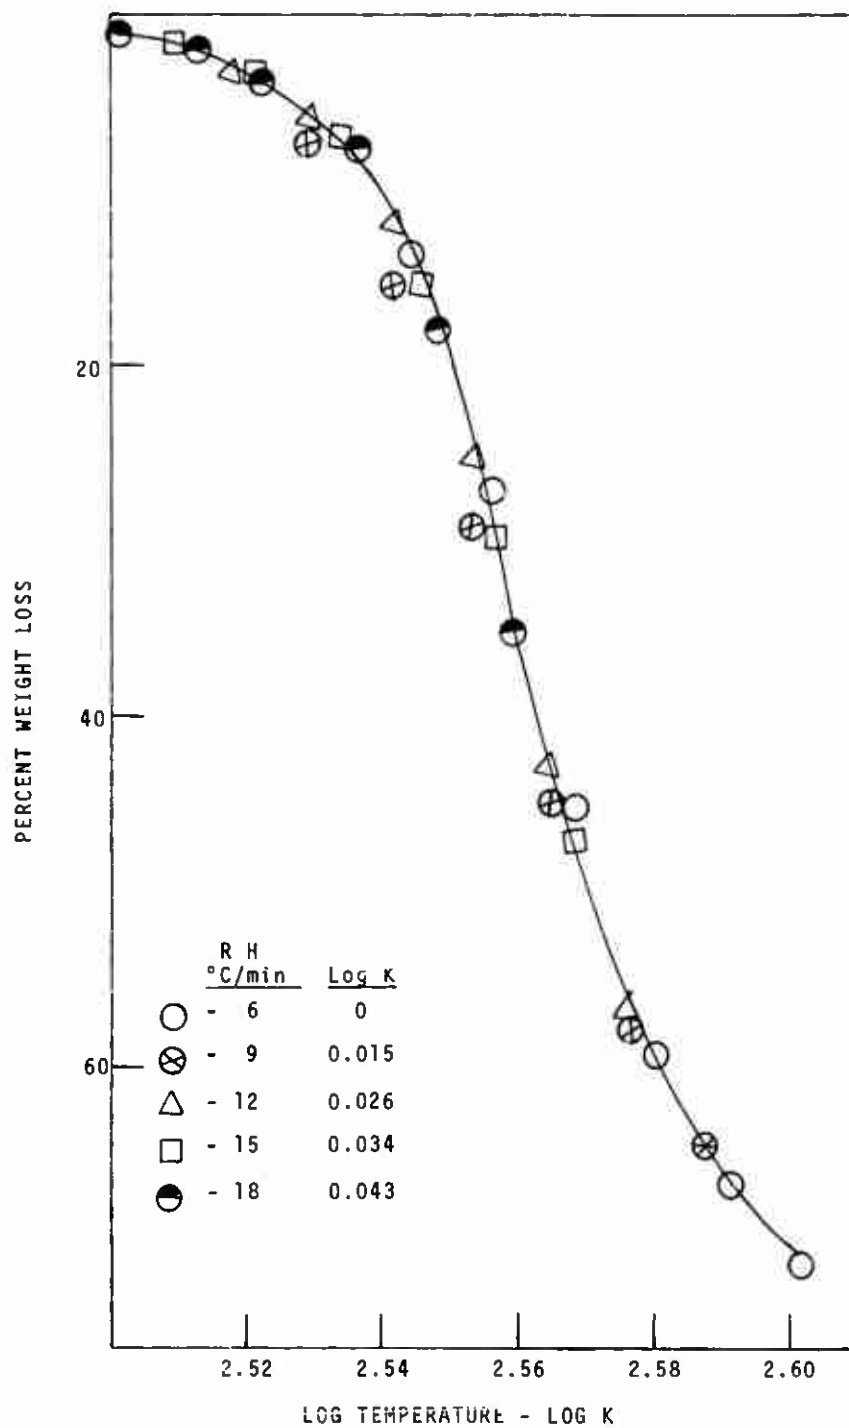


Fig 18 Master curve of weight loss versus temperature for DER 332

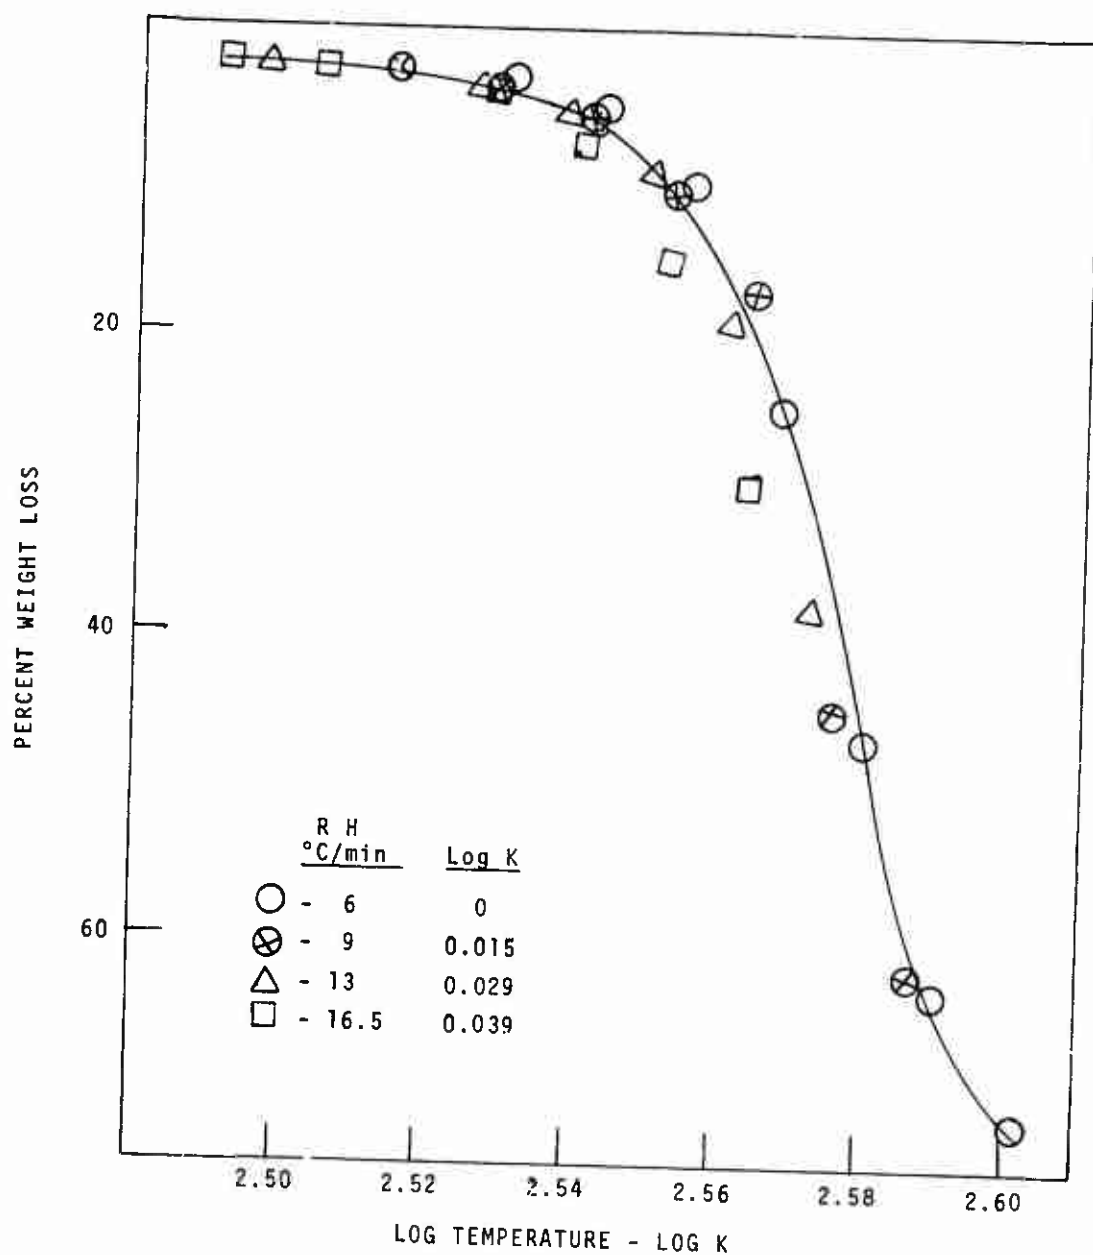


Fig 19 Master curve of weight loss versus temperature for Epon 820

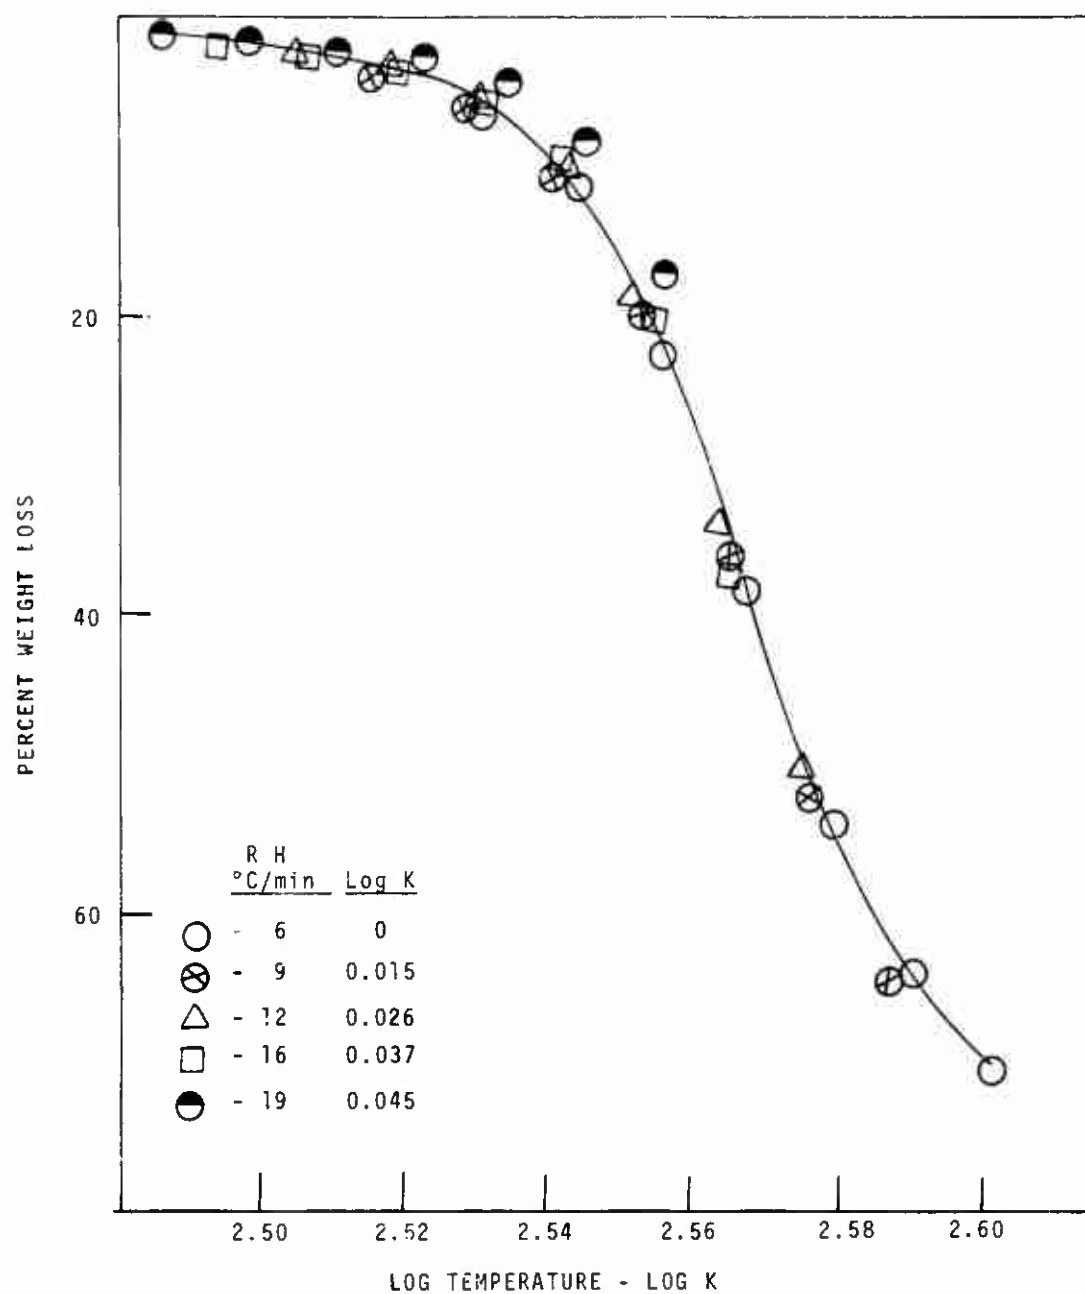


Fig 20 Master curve of weight loss versus temperature for Heptyl

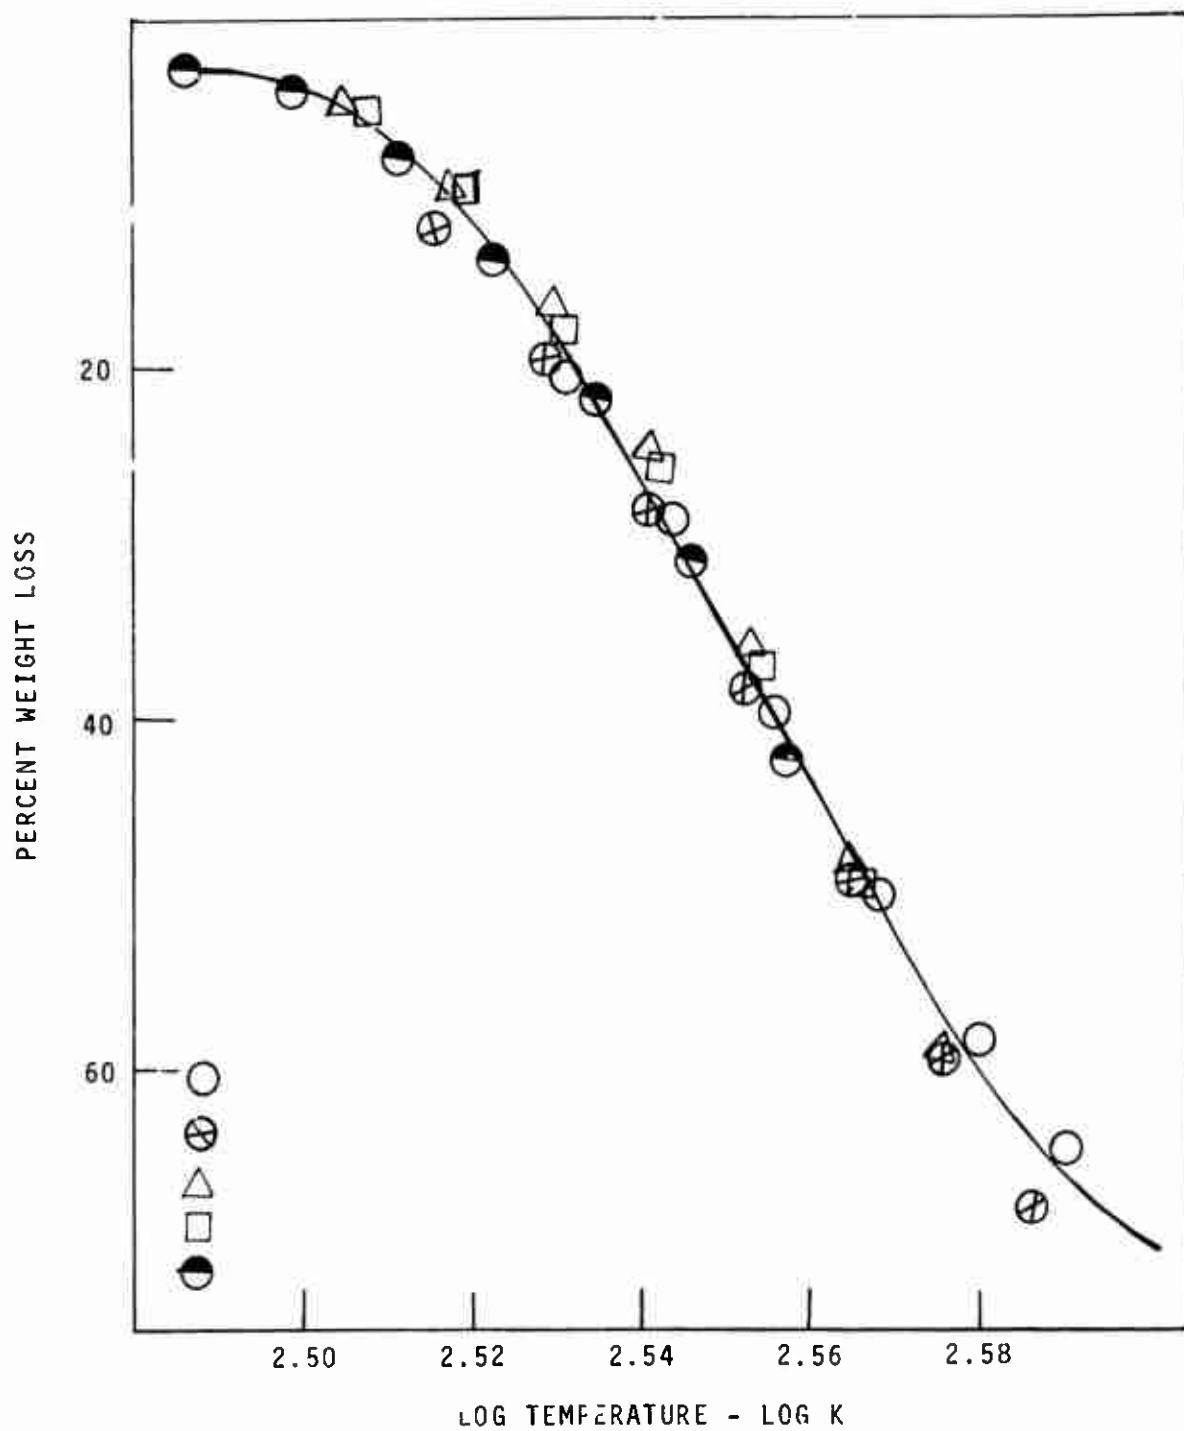


Fig 21 Master curve of weight loss versus temperature for Undecyl

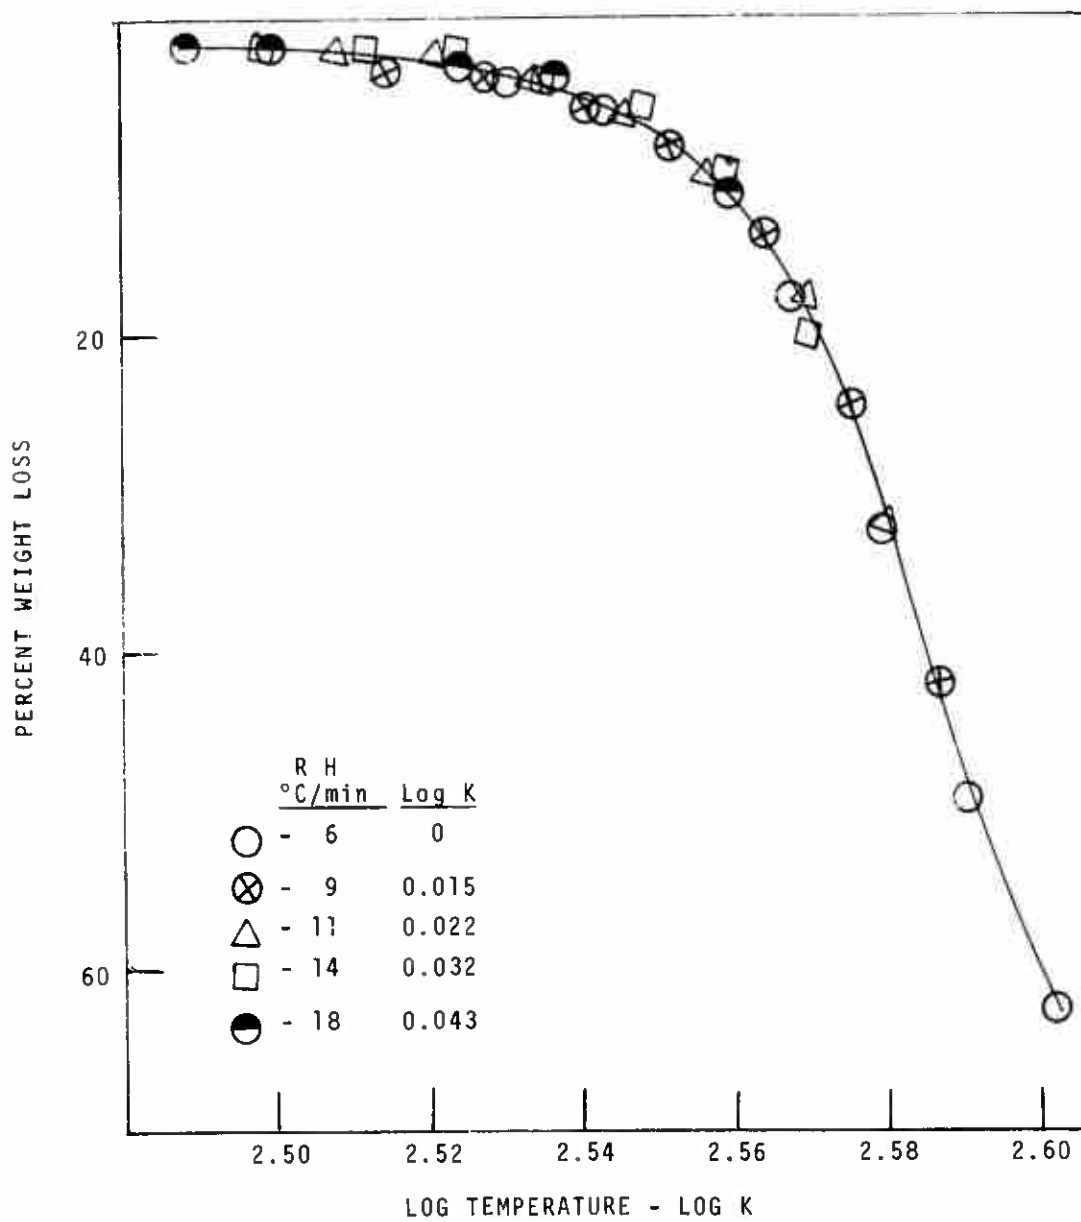


Fig 22 Master curve of weight loss versus temperature for Pentadecyl

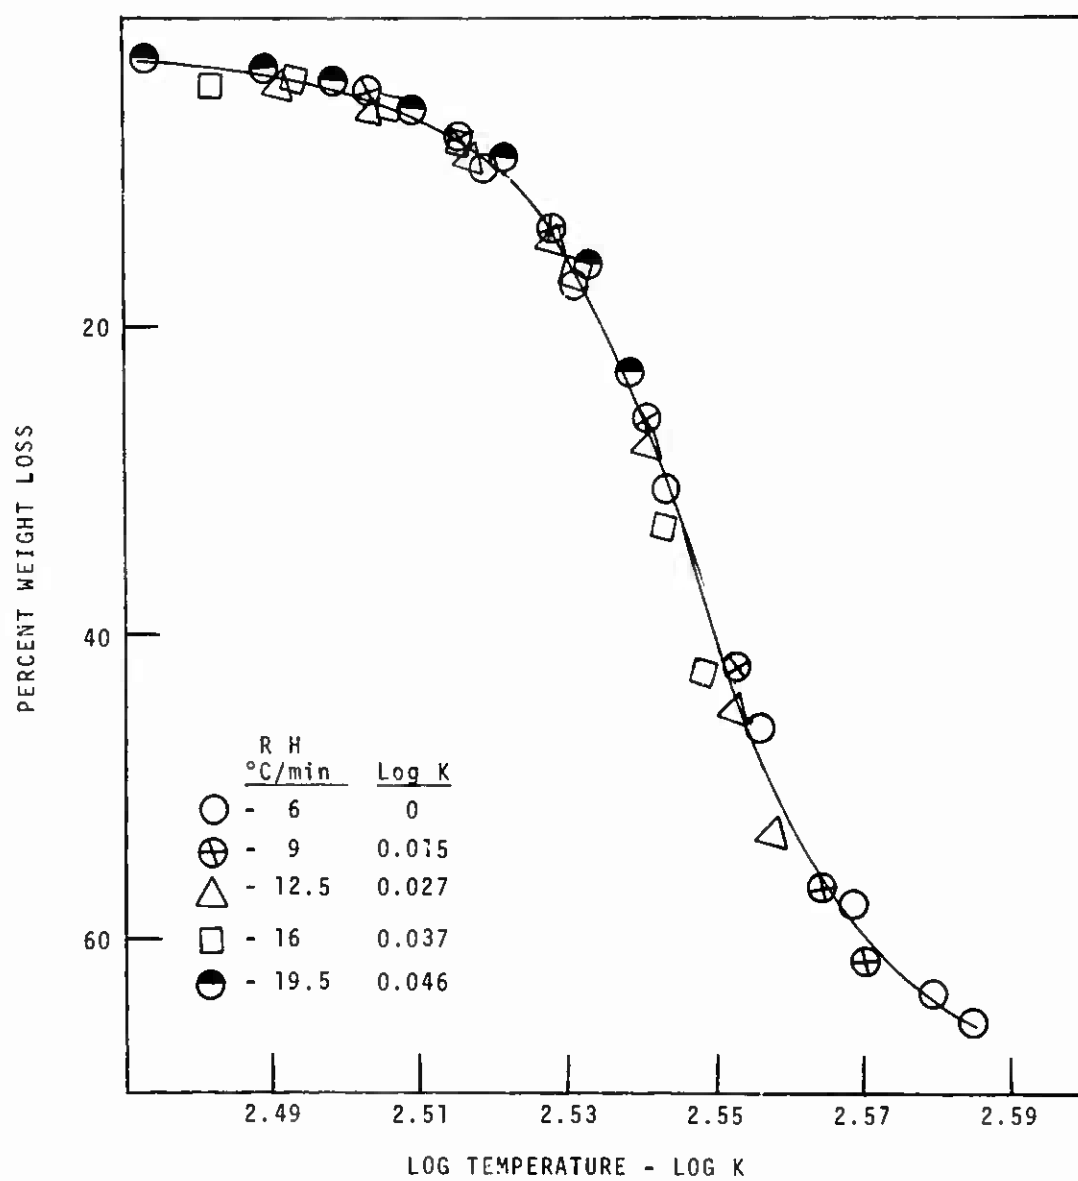


Fig 23 Master curve of weight loss versus temperature for halogenated 6F

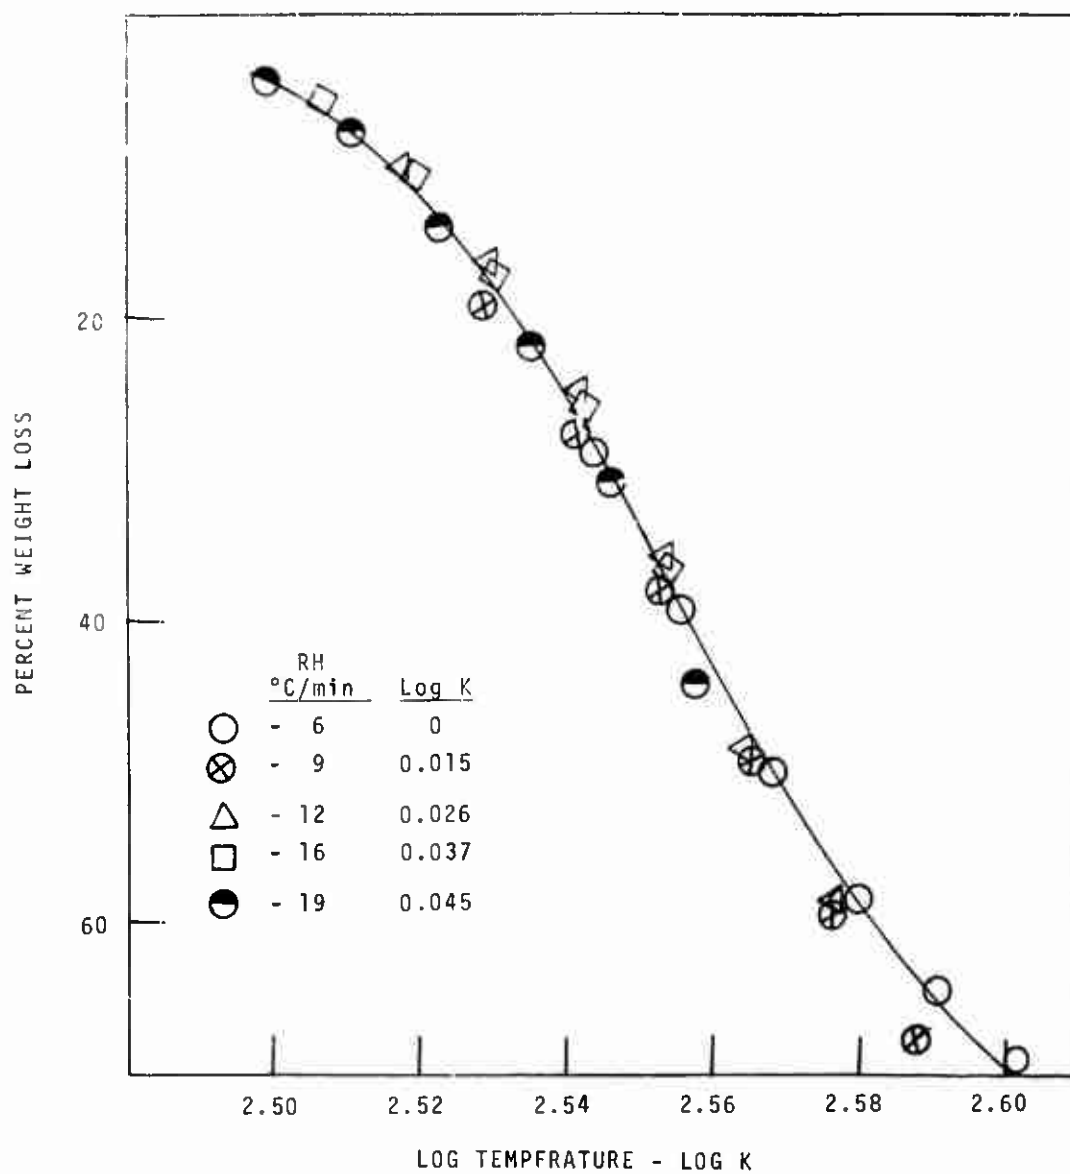


Fig 24 Master curve of weight loss versus temperature for HMDA cured Undecyl